arXiv:1408.6417v1 [cond-mat.mtrl-sci] 27 Aug 2014

# Crystal structure search and electronic properties of alkali doped phenanthrene and picene

S. Shahab Naghavi[1] and Erio Tosatti[1,2]

[1] *International School for Advanced Studies (SISSA), and CNR-IOM Democritos National Simulation Center, Via Bonomea 265, I-34136 Trieste, Italy*
[2] *International Centre for Theoretical Physics (ICTP), Strada Costiera 11, I-34151 Trieste, Italy*

(Dated: August 28, 2014)

Alkali doped aromatic compounds have shown evidence of metallic and superconducting phases whose precise nature is still mysterious. In potassium and rubidium doped phenanthrene, superconducting temperatures around 5 K have been detected, but such basic elements as the stoichiometry, crystal structure, and electronic bands are still speculative. We seek to predict the crystal structure of $M_3$-phenanthrene (M = K, Rb) using *ab-initio* evolutionary simulation in conjunction with density functional theory (DFT), and find metal but also insulator phases with distinct structures. The original $P2_1$ herringbone structure of the pristine molecular crystal is generally abandoned in favor of different packing and chemical motifs. The metallic phases are frankly ionic with three electrons acquired by each molecule. In the nonmagnetic insulating phases the alkalis coalesce reducing the donated charge from three to two per phenanthrene molecule. A similar search for $K_3$-picene yields an old and a new structure, with unlike potassium positions and different electronic bands, but both metallic retaining the face-to-edge herringbone structure and the $P2_1$ symmetry of pristine picene. Both the new $K_3$-picene and the best metallic $M_3$-phenanthrene are further found to undergo a spontaneous transition from metal to antiferromagnetic insulator when spin polarization is allowed, a transition which is not necessarily real, but which underlines the necessity to include correlations beyond DFT. Features of the metallic phases that may be relevant to phonon-driven superconductivity are underlined.

## I. INTRODUCTION

The field of organic superconductors has received recent impulse with the discovery of superconductivity in electron doped picene,[1,2] promptly followed by a broader class of electron-doped polycyclic aromatic hydrocarbons (PAHs). Among them, electron-doped coronene,[3,4] 1,2:8,9-dibenzopentacene,[5] and phenanthrene[6–8] have been reported. To this date, the metallic and superconducting behavior of many of these exciting systems is proving difficult to reproduce[9,10] and there is considerable uncertainty, ranging from stoichiometry, mechanism, and precise crystal structure. To clarify the situation, simultaneous efforts of experiment and theory are called for. The lack of knowledge of stoichiometry and of structure poses a starting dilemma to theory, since calculations, either first principles or modeling, obviously depend on both elements. Most theoretical work so far has assumed the nominal three-electron stoichiometry that seemed closest to that of the superconducting cases, assuming or optimizing crystal structures where six alkali-metal atoms fill a bimolecular unit cell of the same herringbone type as the pristine molecular insulator.[11] Based on these reasonable crystal structures, several superconductivity mechanisms have been discussed for electron-doped PAHs.[4,12–20] However, even modest changes in the orientation and deformation of the PAHs molecules and in the relative position and distance of alkali metal atoms with respect to them and among themselves can alter the bonding nature of the doped system and its electronic structure,[21] making it somewhat risky to build on such insecure foundations. Even assuming without proof the $M_3$-PAHs stoichiometry, a structural search is necessary. The crystal structure searches so far appeared to preserve the pristine herringbone stacking of PAH molecules, limiting the freedom to the alkali atom coordinates and thus exploring only a very small portion of an extensive and complicated phase space. Relaxing this assumption is important, especially as we shall see for small size PAHs.

Predicting crystal structures for organic molecular crystals is not trivial. Intermolecular forces are correlation-dominated and thus hard to determine with confidence by means of standard *ab-initio* density-functional theory (DFT), where correlations are not automatically dealt with. The problem is aggravated by the weakness of these forces, which gives rise to near degeneracies of a confusing variety of structures. Connected with the latter is frank polymorphism, with many competing and coexisting crystalline structures with the same chemical composition but different symmetries and physico-chemical properties,[22] a possibility likely to be important and that should be seriously considered in alkali-doped PAHs. To explore the variety of low energy structural polymorphs an extensive search over the energy landscape of each compound is essential. To the best of our knowledge, search examples from which criteria and trends could be learned ahead of hopeful future experimental verifications are not yet satisfactorily developed for electron doped PAHs.

This paper deals with crystal structure prediction for the computationally simpler PAH compounds $M_3$-phenanthrene ($M_3$-PA),[1,6] and by comparison with the best studied compound, namely $K_3$-picene ($K_3$-PC).[1] To

keep the search as unbiased as possible we resorted to an evolutionary algorithm (EA) whose only required knowledge is chemical composition (see Sec. II for details). It is based on DFT supplemented either by van der Waals (vdW) corrections, which account approximately for some long-range correlation effects, or when more convenient on a hydrostatic pressure suitably tuned to yield equivalent results to vdW. The small unit cell size and the assumed integrity of molecules exclude by construction all possibilities of structural decomposition or polymerization. Despite these limitations, the results reserve interesting and hopefully relevant surprises.

## II. COMPUTATIONAL METHODS

Our search of the stable and low-energy metastable structures was carried out using evolutionary algorithm (EA), as implemented in the USPEX code.[23–27] EA was implemented in conjunction with *ab-initio* structure relaxations based on density functional theory (DFT) within the Perdew-Burke-Ernzerhof (PBE)[28] generalized gradient approximation as implemented in VASP (*Vienna Ab-initio Simulation Package*), [29] employing all-electron projector-augmented plane wave (PAW) method,[30,31] as well as on QUANTUM ESPRESSO.[32,33] Van der Waals forces were included in two different implementations, and separately compared to a simple hydrostatic pressure between 4 and 10 Kbar whose effects after tuning are found to be roughly equivalent to vdW. The stronger chemical bonding involving the alkali atoms, as opposed to the weaker and more delicate intermolecular bonding of pristine PAH crystals makes the use of DFT plus van der Waals more reliable for alkali-doped than for the pristine materials, which would generally require better treatments.[34] Comparison of different calculations provides a picture of the general trends which is both instructive and in our opinion trustworthy. The energy cutoff for the plane-wave basis was set to 550 eV to ensure full convergence, and zero-point energies were not included. The Brillouin zone was sampled by Monkhorst-Pack meshes with the resolution of $2\pi \times 0.05\,\text{Å}^{-1}$. This resolution was decreased to $2\pi \times 0.07\,\text{Å}^{-1}$ to limit the cost of the calculation for $K_3$-PC which has a large unit cell (78 atoms/cell). As a check, we recalculated the final candidate structure with a denser $k$-points sampling and no noticeable change of energy differences between structures emerged.

A strictly trivalent stoichiometry $M_3$-PAH was assumed, each unit cell used in the optimization procedure containing two aromatic molecules and six identical alkali atoms; the molecules could deform but not break. The small unit cell size, 54 atoms of $M_3$-PA (M = K, Rb) and 78 atoms of $K_3$-PC, and the assumed integrity of molecules exclude by construction all possibilities of structural decomposition or polymerization. For the structural search, conducted at zero pressure and temperature, the initial population (the number of structures in starting generation) to densely sample the configuration space. For $M_3$-PA we explored over two thousands structures within about 60 generations to arrive at the converged stable low energy structures. Fig. 1 shows the energy of approximately 1,500 structures (upper panel) calculated at 45 generations (lower panel). This coarse search was done using straight DFT-PBE.

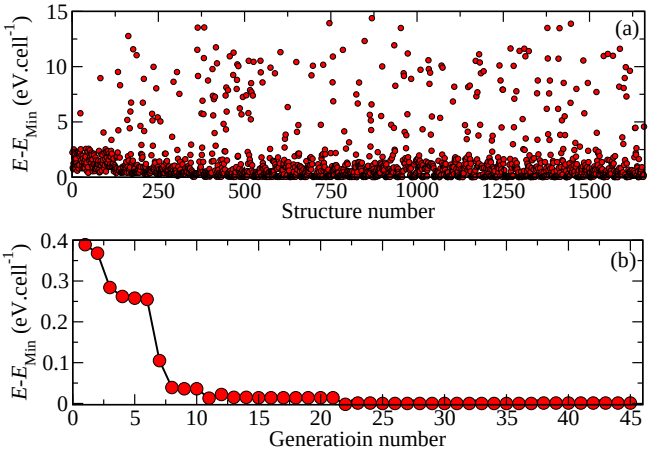


FIG. 1. (Color online) (a) DFT-PBE total energy per dimolecular cell of over 1500 structures of $K_3C_{14}H_{10}$ ($K_3$-PA ) with 54 atoms/cell. (b) Total energy evolution with increasing generation number.

## III. RESULTS

In previous theoretical studies of $M_3$-PA and $K_3$-PC[4,11–20,35,36] the doped PAHs were generally assumed or in some cases found to retain the herringbone arrangements of $P2_1$ symmetry similar to those of the pristine molecular crystals as in Fig. 2. That assumption is not unreasonable, but it is unlikely to be of general validity, and therefore we released it. Especially for the smaller size PAH molecules where direct intermolecular forces are weaker the addition of six alkali atoms per bimolecular per cell is a major perturbation that could impact the herringbone structure. In our EA search for $M_3$-PA (M = K, Rb) and $K_3$-PC, the molecular arrangement was given freedom to change, and in fact the herringbone arrangement was found to survive in $K_3$-PC but not in $M_3$-PA. Below we present results of $M_3$-phenanthrene, (M = K, Rb) first, and for $K_3$-picene second. We will present structures, their energies, and their electronic structures followed by a conclusive discussion.

### A. $M_3$-Phenanthrene (M = K, Rb)

The behavior of $K_3$-PA and of $Rb_3$-PA was found to be totally similar, once a volume expansion of about 8% is considered between the two. Therefore we will mostly

discuss $K_3$-PA here, while all conclusions are valid for $Rb_3$-PA too.

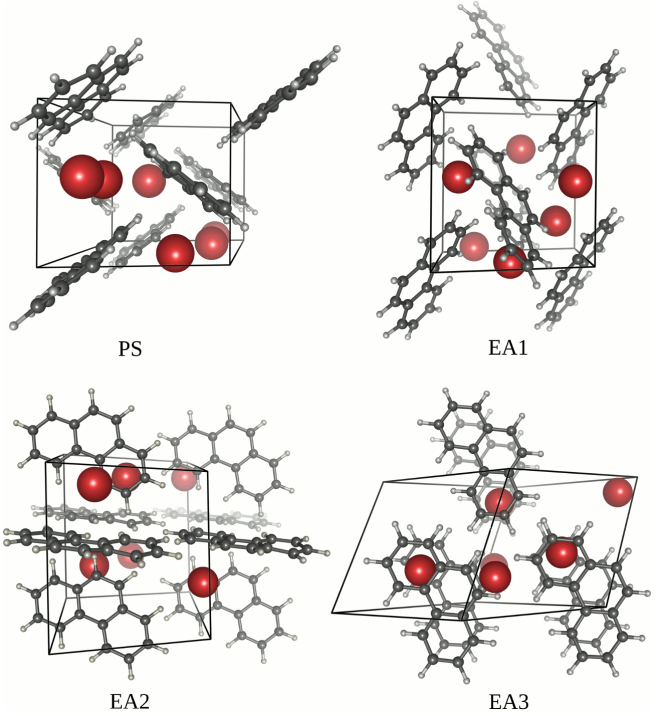


FIG. 2. (Color online) Crystal structures of the $M_3$-PA low energy structures, obtained assuming two PA molecules and six K or Rb atoms per cell. PS is the previous $P2_1$ symmetry herringbone structure of de Andres et al,[11], chosen as reference. Structure EA1 (metallic) is a first evolution of PS; EA2 (insulating) and EA3 (metallic) are the two lowest energy structural polymorphs. All have a lower $P_1$ symmetry, but differ by arrangement and shape details of the phenanthrene molecules, and by the positions of the alkalis. Note that approximately defined molecular planes are nearly orthogonal in EA2, but have turned parallel in EA3, which represents our best candidate metallic (possibly superconducting) phase.

We obtained the three lowest energy structures EA1–3 of Fig. 2, with lattice parameters listed in Table I. Full crystal structure data is given in the Supplementary Information in *cif* format at the end of this manuscript. The three structures differ in the orientation (and distortion) of the phenanthrene molecules and in the position of the alkali atoms in the bimolecular cell. Each of these structures, generally with $P_1$ symmetry, represents a "relevant structure", standing for a multiplicity of nearly degenerate structures differing, e.g., by small displacements of alkali atoms or small distortions of the PA molecules. Later we will provide for the best metallic structure EA3 an example of such a slightly distorted structure which turns the crystal from metallic to semimetallic. Total energies and structural parameters are presented in Fig. 3, also illustrating the uncertainty due to the different vdW functional chosen, as well as a rough equivalence of some vdW forces to a hydrostatic pressure.

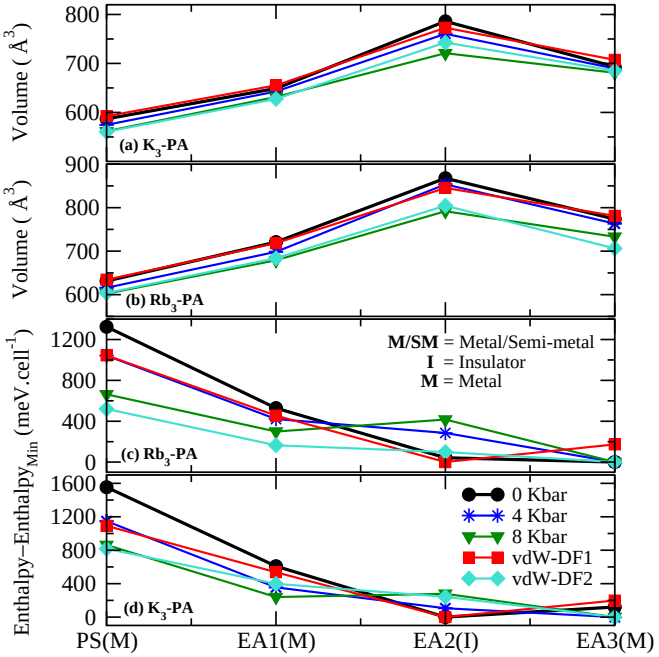


FIG. 3. (Color online) Cell volume and enthalpy of the most stable $K_3$-PA and $Rb_3$-PA candidate structures. After a DFT-PBE genetic search, the lowest energy structures were refined with vdW functionals or with increasing pressure.

The first relevant structure EA1 is a herringbone although a different one from PS [11] with a 0.4–0.8 eV/cell lower energy, as seen in Fig. 3. Molecules in EA1 are T-shape oriented and are stacked long edge-to-face, with an angle of about 70°. The DFT-PBE electronic structure calculation (Fig. 4) shows that EA1 is metallic, but with much narrower bands and lower symmetry than PS.

In structure EA2 the PA molecules approximately lie on alternating nearly orthogonal planes and are relativel flat, but the six alkali atoms are grouped close enough together to form a sort of loose cluster, sitting between the molecules. The formation energy of $M_3$-PA compounds relative to the metallic alkali metal plus pristine phenanthrene is definitely negative,[37] which rules out phase separation, which would be surprising here even if in an embryonic form. In order to understand what happens we carried out an analysis of the bonding which is shown in Fig.5, and of the resulting electronic structure, Fig.4.

The outcome is that in EA2 the $M_6$ alkali cluster as a whole donates four of its six *s*-electrons to the LUMO orbitals of the two PAH molecules in the cell, leaving the LUMO+1 totally empty. The two remaining alkali *s*-electrons fill up instead a "superatomic" orbital of the alkali cluster, emphasized in Fig.4, with energy well below the Fermi energy and even below the LUMO band. This electronic configuration gives rise to an insulator with a gap of 0.2–0.4 eV, roughly corresponding to the LUMO-LUMO+1 energy separation. The EA2 structure is therefore not a straight phase separation in an embryonic stage but rather appears to represent, with all

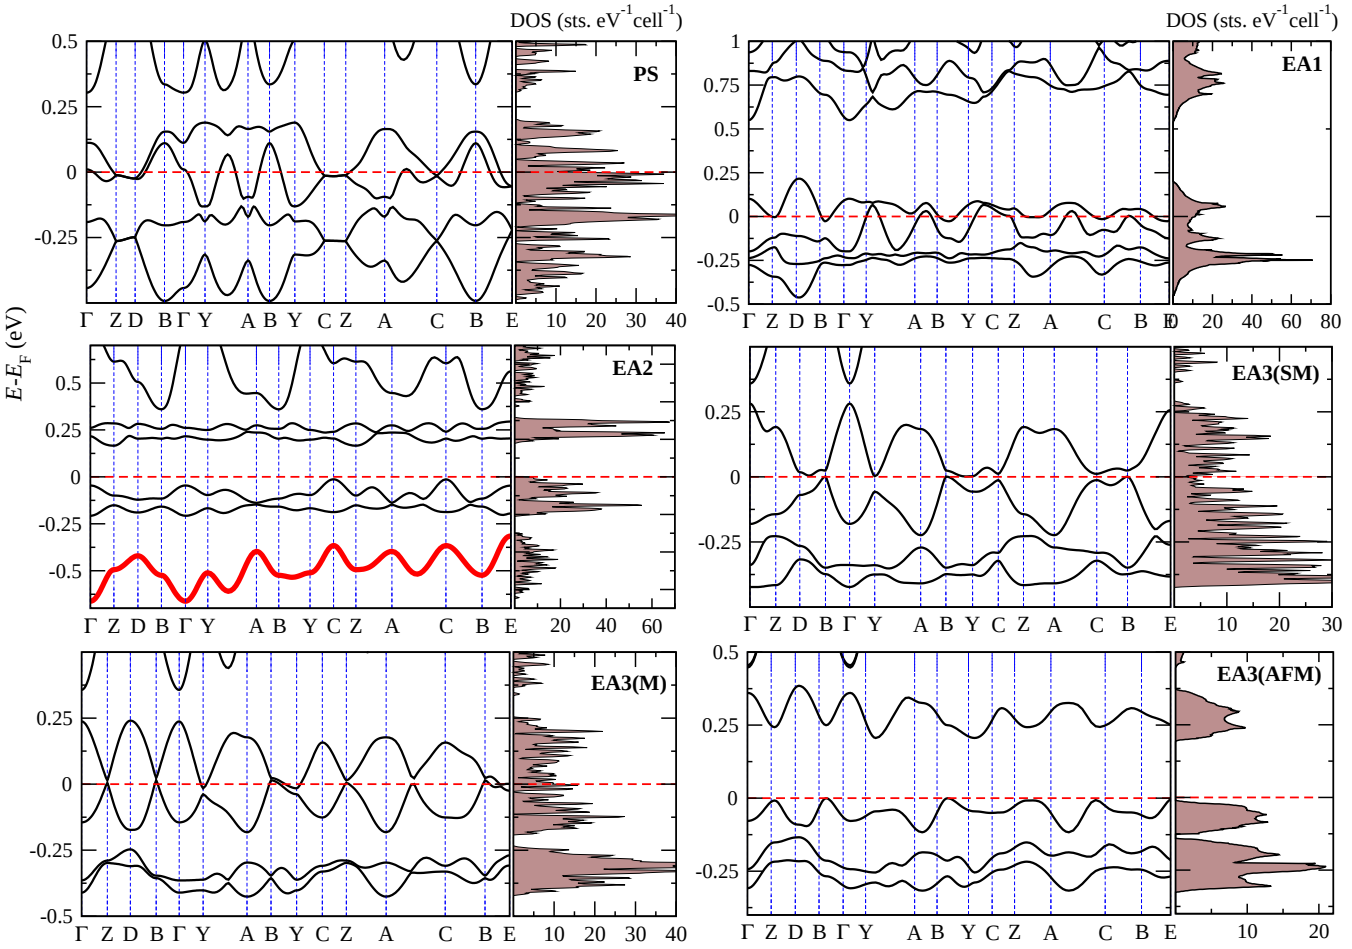


FIG. 4. (Color online) DFT-PBE electronic band structure of various $K_3$-PA crystal structures. Among the two best structures EA2 and EA3, EA2 is a nonmagnetic band insulator, where the two uppermost filled bands have molecular LUMO character, the lowest unfilled bands a LUMO+1 character, and the filled band emphasized in red is a shared orbital within the six alkali atoms in the cell. EA3 instead is the best metallic structure with partly degenerate LUMO+1 half filled bands at Fermi level, not unlike those calculated for La-PA.[20]. In analogy to that case, the near-degeneracy at Fermi can be reduced or lifted by a slight intra-cell atomic displacement (here of the K atoms) which takes the system to a semi-metallic state. The insulating antiferromagnetic electronic structure obtained by allowing spin polarization in metallic EA3 is also shown.

the caution and the provisos suggested by assumptions made about cell size and about stoichiometry, a true polymorph of $M_3$-PA. Its structure enhances the crystal volume with a large intermolecular distance between the phenanthrene molecules, yet the mixed ionic-covalent bonding makes it energetically competitive. Of course, unusual as this structure is, it would need checking, e.g., by increasing the simulation cell size, for example by doubling it in the form (2x2x2). However, that would call for a $2^6$ times large computational effort which is presently beyond the reach of this work. Because of that, and since EA2 is not always the lowest energy structure at least in presence of van der Waals forces, and is not even metallic, we do not pursue it further.

Structure EA3 finally, our best metallic structure, is characterized by a remarkably different, parallel stacking of phenanthrene molecular layers repeating on top of one another (AAA) with alkali atoms spread between the layers as in Fig. 2. The electronic structure of Fig.4 shows half-filled LUMO+1 bands of width 0.2 eV that are half-filled and somewhat close to electron-hole symmetrical, with near degeneracies and a high density of states near the Fermi level. As was the case in a model previously derived for the hypothetical crystal La-phenanthrene,[20] this situation suggests a potentially strong Fröhlich electron-phonon coupling to zone boundary modes. Among them, a distortion that would reduce the approximate equidistance of atoms and of molecules in the cell, removes this degeneracy and leads to a semimetal.[20] Modifying the structure EA3 of $K_3$-PA by statically displacing the alkali atoms out of their optimal straight-line arrangement (Fig. 6) for example to form an angle of about 174° rather than 180°, the band splitting and the resulting semimetallic behavior obtained are shown in Fig. 4. This is a suggestive element in view of a possible electron-phonon mechanism for superconductivity of electron-

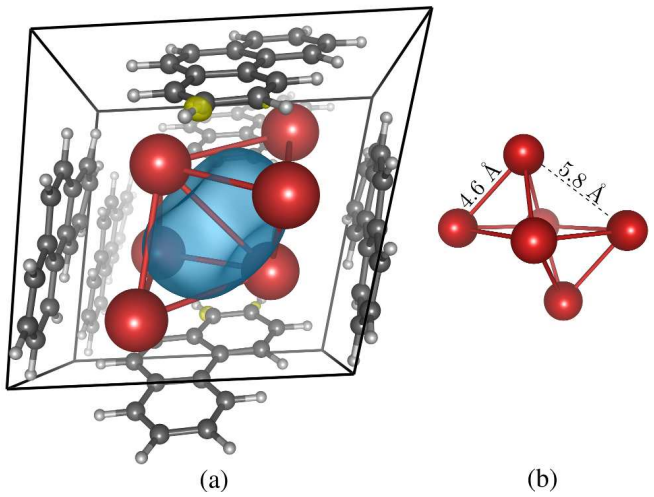


FIG. 5. (Color online) Electron density portrait $|\Psi(r)|^2$ of the filled orbital shown as a red band in Fig. 4 for the EA2 nonmagnetic insulating structure of $K_3$-PA. Coordinates were chosen to emphasize the shared nature of this orbital between the six clustered K atoms.

doped PAHs, which is presently under discussion and is being addressed elsewhere.[38] The gap-opening distortion just chosen here is of course somewhat arbitrary, and a proper phonon and electron-phonon calculation will be needed in order to pursue this line.

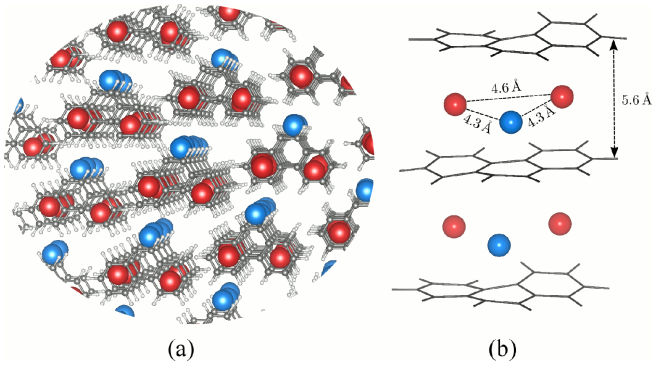


FIG. 6. (Color online) Top view of the EA3 structure of $K_3$-PA. K atoms are aligned in a slightly deformed straight line with a $K_1$–$K_2$–$K_3$ angle of 174°. An increased zig-zag deformation reducing this angle to 162° transforms the metal into a semi-metal. The distance between the phenanthrene molecular centers is about 5.5 Å, that between the K and center of the nearest benzene ring of PA 2.7 Å. The PA molecules, although not strictly planar, approximately lie on parallel planes, in contrast with the herringbone structure of pristine phenanthrene and of structure EA1.

### B. $K_3$-Picene

The genetic crystal structure optimization just conducted for $M_3$-PA led to identify unexpected structures, where the pristine herringbone molecular stacking is abandoned. In view of that, it is worthwhile conducting the same search for $K_3$-PC. Repeating for better confidence the search with a variety of different starting points and both with DFT-vdW and with DFT-PBE at 10 kbars which are roughly equivalent, we invariably found in $K_3$-picene a face-to-edge herringbone packing as the best structure, in contrast to $M_3$-PA. This supports the assumptions and the results , anticipated by previous authors, that the basic herringbone structural motif of pristine picene is preserved.[18,36].

Previous studies of acenes emphasized the importance of the balance between electrostatic and van der Wals interactions for the packing in molecular crystals.[39,40] As discussed for pentacene,[39] co-planar stacking essentially results from electrostatic interaction while face-to-edge herringbone is stabilized by dispersion and quadrupole forces. The much larger size of picene implies larger quadrupolar forces, which explains the large stability of herringbone, as opposed to the fragility against doping just shown for phenanthrene.

Both C and D structures, that are energetically the best in presence of van der Waals forces, are face-to-edge herringbone with $P2_1$ symmetry (Fig.7 and Fig.8). Similarly to the previously optimized $K_3$-PC-structure[36] the potassium atoms form ordered chains along the $c$-axis, lying in front of the aromatic ring (Fig.7). In structure D the chains are uniformly stacked, whereas in the ordering

TABLE I. Energy and structural data of the best structures of $K_3$-PA and $Rb_3$-PA calculated with DFT- GGA at zero pressure compared with the earlier proposed PS structure.[11]. Energy in units of meV.cell$^{-1}$ measured with respect to that of the best structure. Volume is in Å$^3$. Each of these relevant structures generally allows slightly different variants depending on small extra alkali or molecular displacements.

| | PS(M) | EA1(M) | EA2(I) | EA3(SM) | EA3(M) |
|---|---|---|---|---|---|
| | | | $K_3$-PA | | |
| Sym. | P21 | P21 | P1 | P1 | P1 |
| Energy | 1352 | 556 | 70 | 28 | 0 |
| Volume | 586.9 | 648.8 | 786.0 | 693.4 | 725.7 |
| $a$ | 8.24 | 8.95 | 9.63 | 9.96 | 10.20 |
| $b$ | 7.05 | 8.32 | 9.89 | 8.92 | 9.12 |
| $c$ | 10.7 | 8.9 | 9.5 | 9.5 | 9.6 |
| $\alpha$ | 90.0 | 103.0 | 112.6 | 95.1 | 97.2 |
| $\beta$ | 108.8 | 90.0 | 90.7 | 114.2 | 107.8 |
| $\gamma$ | 90.0 | 90.0 | 100.7 | 64.9 | 116.2 |
| | | | $Rb_3$-PA | | |
| Sym. | P21 | P21 | P1 | P1 | P1 |
| Energy | 1554 | 608 | 0 | 129 | 120 |
| Volume | 631 | 721 | 868 | 765 | 774 |
| $a$ | 8.74 | 9.16 | 9.87 | 10.32 | 10.23 |
| $b$ | 7.10 | 8.64 | 10.12 | 9.13 | 9.18 |
| $c$ | 10.78 | 9.26 | 9.64 | 9.82 | 9.79 |
| $\alpha$ | 90.0 | 100.6 | 113.4 | 94.9 | 96.0 |
| $\beta$ | 109.4 | 90.0 | 90.8 | 112.2 | 106.2 |
| $\gamma$ | 90.0 | 90.0 | 99.9 | 63.7 | 115.0 |

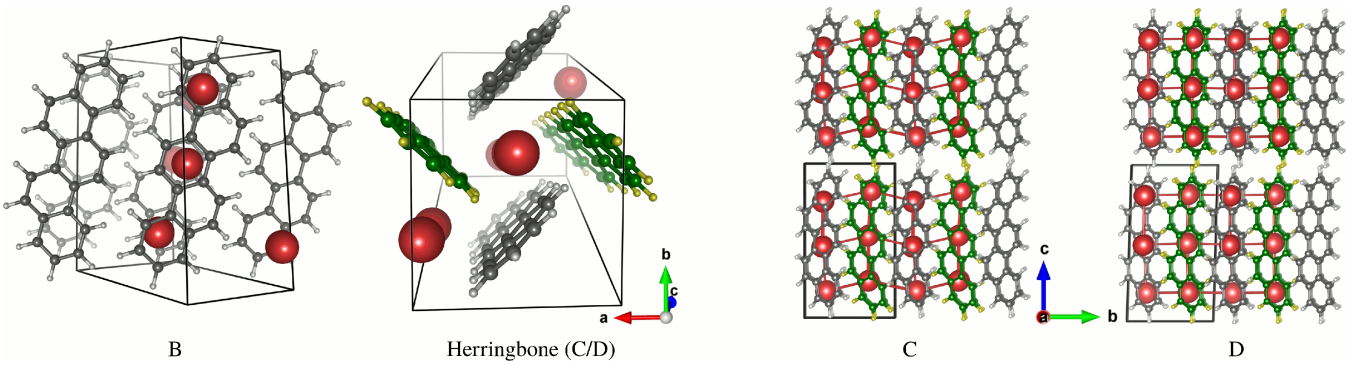


FIG. 7. (Color online) The three best structures B,C, D of $K_3$-picene. All structures are herringbone with $P2_1$ symmetry as in pristine molecular picene. D basically coincides with a previously proposed structure[36], whereas in C alternating lines of potassium atoms are shifted relative to one another, forming a zig-zag network. C and D have basically the same total energy.

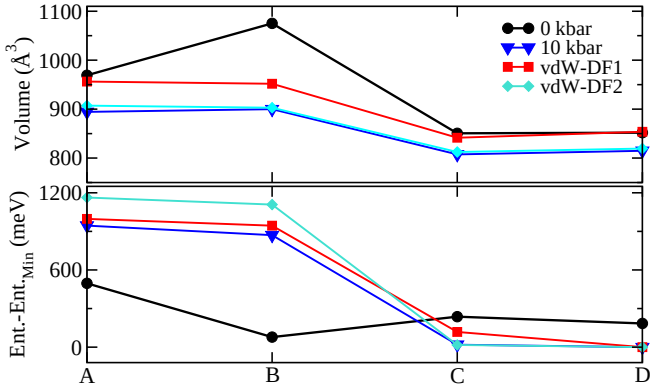


FIG. 8. (Color online) Volume (a) and enthalpy (b) of four relevant structures A–D of $K_3$-PC using different functionals and at different pressures. Structure D is closest to earlier established structure in Ref.[36] The two best structures C and D are nearly degenerate in energy and differ by the fractional shift of one alkali line relative to the other line in the unit cell. Note that here vdW corrections are more important than in $M_3$-PA, on account of the larger molecular size. A hydrostatic pressure of about 10 kbars (blue line) has here a similar effect to vdW-DF (cyan and red lines).

is zigzag shifted along the $b$-axis, so that the potassium atoms are located in front of the C–C bond instead of the aromatic ring center.

In spite of the similarity between the two structures, their electronic band structures are quite different. As seen in Fig. 9, C has narrow bandwidths (the strongest hopping parameter in the LUMO+1 band is 0.02 eV) and LUMO, and LUMO+1 are narrow and well separated. A high density of states at Fermi energy together with the narrow bandwidth lead to instability in the system, prone to magnetism or to a structural distortion, or else to superconductivity. We find that antiferromagnetic ordering lowers the energy of C by 40 meV/bimolecular cell, whereas the antiferromagnetic total energy gain in D is only 20 meV/bimolecular cell, a smaller value due to residual band overlap and metallicity.

We stress here that this kind antiferromagnetic instability of the metallic phases, well known and quite general for these narrow band systems,[17] must be considered with caution. It is surely a signal warning that correlations are very strong, but it needs not imply a true instability of the metallic state. As is independently being shown e.g., in Ref[38] the inclusion of correlations through a Gutzwiller treatment of a Hubbard $U$ can upset the energetic balance between the metal and the antiferromagnetic insulator, actually favoring a nonmagnetic, metallic and potentially superconducting state at least for small $U$. This background knowledge allows the provisional neglect of the magnetic instabilities, and a serious consideration of crystal structures C and D as genuine candidates describing the metallic phase of $K_3$-PC.

## IV. CONCLUSIONS

Electron doped PAHs encompass a larger variety of crystal structure polymorphs than imagined so far. We systematically studied the crystal structure of $M_3$-PA (M = Rb and K), an interesting system where superconductivity has been reported, and of $K_3$-PC, the most studied electron doped and superconducting PAH. By means of an evolutionary algorithm we identified in $K_3$-PA and $Rb_3$-PA at least two possible polymorphs with distinctly different structures that are competing for the ground state. One of them (EA2) is a band insulator, the other (EA3) is metallic, and thus a candidate superconductor. Structurally, the pristine herringbone structural symmetry appears systematically broken by the alkali doping.

The scenario is different in $K_3$-PC, where the larger size molecule allows to the herringbone structure and $P2_1$ symmetry to survive in the stable structure. Here too we still find two essentially degenerate polymorphs, both metallic, whose only difference is the arrangement of the potassium atoms.

Within DFT-PBE all metallic structures are unstable against antiferromagnetism, an instability which leads them to an insulating state in pin-polarized DFT. While

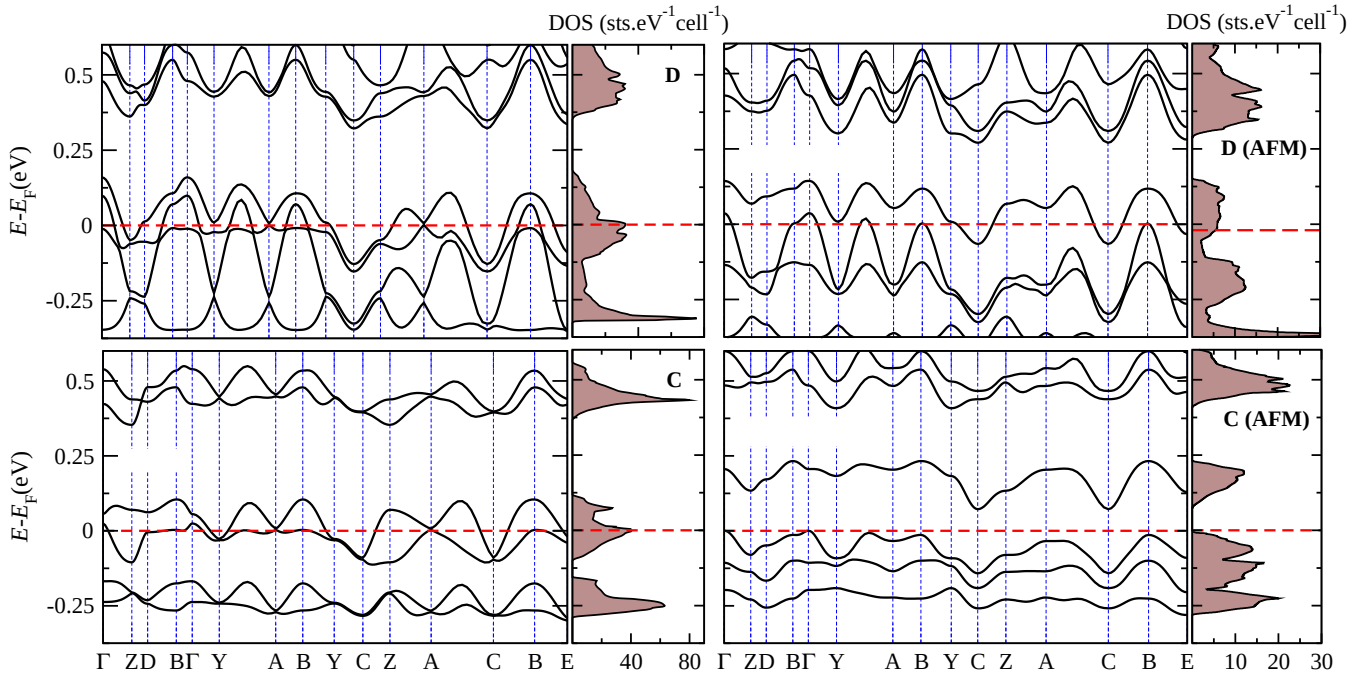


FIG. 9. (Color online) Electronic band structure of structures C and D of $K_3$-PC in the non-magnetic (left) and antiferromagnetic state (right). Structure C has narrower bands, and gains 40 meV per dimolecular cell upon antiferromagnetic ordering, while in the broader-band crystal structure D the gain is about 20 meV. The energy lowering in the antiferromagnetic insulators signals the importance of correlations, more than a real magnetic instability of the metallic state.[38]

that signals the importance of correlations in the non-magnetic metallic states, it does not imply their irrelevance or non-existence, as recent Gutzwiller calculations have suggested.[38]

Should the three-electron stoichiometry which we assumed beconfirmed, the present results would also be relevant to the superconductivity of these compounds. The electronic structures of most metallic phases we found, either $M_3$-PA or $K_3$-PC, share a common element, namely the near degeneracy among the two LUMO+1 half-filled conduction bands, quite close to the Fermi level. That degeneracy may, as was noted in an earlier calculation for hypothetical La-PA, [20] and as is pointed out above for structure EA3 of $K_3$-PA be very efficiently split by a zone boundary phonon. That is in broad analogy with $MgB_2$, potentially interesting as a driving element of phonon-driven superconductivity. Our recent study of a "Hubbard-Frohlich" model derived by idealizing this idea is showing a $s_{\pm}$ superconducting phase which is especially robust against electron-electron repulsion.[38].

Comparison of our theoretical crystal structures with experiments, problematic at the moment because well defined single phase stoichiometrically defined data are still being sought, will be very interesting suggesting a close cooperation with future structural determinations. We underline the fact that structural work and chemical understanding represent an absolutely vital and urgent necessity for the development and credibility of this field. The present theory work is a basic contribution to this development, that will hopefully encourage future experimental work.

## ACKNOWLEDGMENTS

This work was supported by the European Union FP7-NMP-2011-EU-Japan project LEMSUPER and in part by PRIN/COFIN Contract PRIN-2010LLKJBX_004 as well as a collaboration with Argonne National Laboratories. We acknowledge discussions with LEMSUPER members, with our SISSA group members M. Capone, M. Fabrizio, and T. Qin. A CINECA award 2013 of high performance computing resources was instrumental to the realization of this work.

[1] R. Mitsuhashi, Y. Suzuki, Y. Yamanari, H. Mitamura, T. Kambe, N. Ikeda, H. Okamoto, A. Fujiwara, M. Yamaji, N. Kawasaki, Y. Maniwa, and Y. and, Nature **464**, 76 (2010).

[2] G. Artioli and L. Malavasi, J. Mater. Chem. C **2**, 1577 (2014).

[3] Y. Kubozono, H. Mitamura, X. Lee, X. He, Y. Yamanari, Y. Takahashi, Y. Suzuki, Y. Kaji, R. Eguchi, K. Akaike, T. Kambe, H. Okamoto, A. Fujiwara, T. Kato, T. Kosugi, and H. Aoki, Phys. Chem. Chem. Phys. **13**, 16476 (2011).

[4] T. Kato, T. Kambe, and Y. Kubozono, Phys. Rev. Lett. **107**, 077001 (2011).

[5] M. Xue, T. Cao, D. Wang, Y. Wu, H. Yang, X. Dong, J. He, F. Li, and G. F. Chen, Sci. Rep. **2**, 389 (2012).

[6] X. Wang, R. Liu, Z. Gui, Y. Xie, Y. Yan, J. Ying, X. Luo, and X. Chen, Nature Commun. **2**, 507 (2011).

[7] X. F. Wang, Y. J. Yan, Z. Gui, R. H. Liu, J. J. Ying, X. G. Luo, and X. H. Chen, Phys. Rev. B **84**, 214523 (2011).

[8] X. F. Wang, X. G. Luo, J. J. Ying, Z. J. Xiang, S. L. Zhang, R. R. Zhang, Y. H. Zhang, Y. J. Yan, A. F. Wang, P. Cheng, G. J. Ye, and X. H. Chen, J. Phys. Condens. Matter **24**, 345701 (2012).

[9] B. Mahns, F. Roth, and M. Knupfer, J. Chem. Phys. **136**, 134503 (2012).

[10] M. Caputo, G. D. Santo, P. Parisse, L. Petaccia, L. Floreano, A. Verdini, M. Panighel, C. Struzzi, B. Taleatu, C. Lal, , and A. Goldoni, J. Phys. Chem. C **116**, 19902 (2012).

[11] P. L. de Andres, A. Guijarro, and J. A. Vergés, Phys. Rev. B **84**, 144501 (2011).

[12] A. Subedi and L. Boeri, Phys. Rev. B **84**, 020508 (2011).

[13] M. Casula, M. Calandra, G. Profeta, and F. Mauri, Phys. Rev. Lett. **107**, 137006 (2011).

[14] M. Casula, M. Calandra, and F. Mauri, Phys. Rev. B **86**, 075445 (2012).

[15] T. Kosugi, T. Miyake, S. Ishibashi, R. Arita, and H. Aoki, Phys. Rev. B **84**, 214506 (2011).

[16] T. Kosugi, T. Miyake, S. Ishibashi, R. Arita, and H. Aoki, J. Phys. Soc. Jpn. **78**, 113704 (2009).

[17] G. Giovannetti and M. Capone, Phys. Rev. B **83**, 134508 (2011).

[18] A. Ruff, M. Sing, R. Claessen, H. O. J. H. Lee, M. Tomić, and R. Valentí, Phys. Rev. Lett. **110**, 216403 (2013).

[19] M. Kim, H. C. Choi, J. H. Shim, and B. I. Min, New J. Phys. **15**, 113030 (2013).

[20] S. S. Naghavi, M. Fabrizio, T. Qin, and E. Tosatti, Phys. Rev. B **88**, 115106 (2013).

[21] T. A. Baker and M. Head-Gordon, J. Phys. Chem. A **114**, 10326 (2010).

[22] J. Bernstein, Polymorphism in Molecular Crystals (Oxford University Press, 2007).

[23] C. W. Glass, A. R. Oganov, and N. Hansen, Comput. Phys. Commun. **175**, 713 (2006).

[24] A. R. Oganov and C. W. Glass, J. Chem. Phys. **124**, 244704 (2006).

[25] A. O. Lyakhov, A. R. Oganov, H. T. Stokes, and Q. Zhu, Comput. Phys. Commun. **184**, 1172 (2013).

[26] A. R. Oganov, A. O. Lyakhov, and M. Valle, Acc. Chem. Res. **44**, 227 (2011).

[27] Q. Zhu, A. R. Oganov, C. W. Glass, and H. T. Stokes, Acta Crystallogr. Sect. B **68**, 215 (2012).

[28] J. P. Perdew, K. Burke, and M. Ernzerhof, Phys. Rev. Lett. **78**, 1396 (1997).

[29] G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11169 (1996).

[30] P. E. Blöchl, Phys. Rev. B **50**, 17953 (1994).

[31] G. Kresse and D. Joubert, Phys. Rev. B **59**, 1758 (1999).

[32] P. Giannozzi *et al*, J. Phys. Condens. Matter **21**, 395502 (2009).

[33] R. Sabatini, E. Kücükbenli, B.Kolb, T. Thonhauser, and S. de Gironcoli, J. Phys. Condens. Matter **24**, 424209 (2012).

[34] K. Hongo, M. A. Watson, R. S. Sánchez-Carrera, T. Iitaka, and A. Aspuru-Guzik, J. Phys. Chem. Lett. **1**, 1789 (2010).

[35] A. Hansson, J. Böhlin, and S. Stafström, Phys. Rev. B **73**, 184114 (2006).

[36] P. L. de Andres, A. Guijarro, and J. A. Vergés, Phys. Rev. B **83**, 245113 (2011).

[37] X.-W. Yan, Z. Huang, and H.-Q. Lin, arXiv:1407.0747v1.

[38] T. Qin, M. Fabrizio, S. Naghavi, and E. Tosatti, to be published (2014).

[39] D. Käfer, M. E. Helou, C. Gemel, and G. Witte, Cryst. Growth Design. **8**, 3053 (2008).

[40] T. Janowski, A. R. Ford, and P. Pulay, Mol. Phys. **108**, 249 (2010).

# SUPPLEMENTARY: CRYSTALLOGRAPHIC INFORMATION FILE (CIF)

## A. $M_3$-phenanthrene

### 1. Structure *EA1*

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_EA1


_pd_phase_name                         'EA128   8.936  8.282  8.918 102.934 89'
_cell_length_a                         8.94969
_cell_length_b                         8.31950
_cell_length_c                         8.94544
_cell_angle_alpha                      103.03106
_cell_angle_beta                       89.53737
_cell_angle_gamma                      89.61511
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.236961      0.768231      0.097236     Biso  1.000000 C
   C2         1.0     0.195296      0.631071      0.156179     Biso  1.000000 C
   C3         1.0     0.149564      0.813722      0.981541     Biso  1.000000 C
   C4         1.0     0.063940      0.541797      0.099717     Biso  1.000000 C
   C5         1.0     0.012977      0.729514      0.925556     Biso  1.000000 C
   C6         1.0     0.970017      0.585593      0.987782     Biso  1.000000 C
   C7         1.0     0.921665      0.775133      0.816305     Biso  1.000000 C
   C8         1.0     0.561874      0.319951      0.831266     Biso  1.000000 C
   C9         1.0     0.654613      0.266666      0.936170     Biso  1.000000 C
   C10        1.0     0.601150      0.463035      0.776453     Biso  1.000000 C
   C11        1.0     0.787108      0.356064      0.988246     Biso  1.000000 C
   C12        1.0     0.740083      0.550975      0.820339     Biso  1.000000 C
   C13        1.0     0.833489      0.496517      0.935155     Biso  1.000000 C
   C14        1.0     0.787643      0.685189      0.762353     Biso  1.000000 C
   C15        1.0     0.746751      0.849955      0.274673     Biso  1.000000 C
   C16        1.0     0.695812      0.981149      0.211726     Biso  1.000000 C
   C17        1.0     0.662118      0.802331      0.392553     Biso  1.000000 C
   C18        1.0     0.559853      0.064903      0.268233     Biso  1.000000 C
   C19        1.0     0.519386      0.878206      0.445960     Biso  1.000000 C
   C20        1.0     0.470964      0.021866      0.385538     Biso  1.000000 C
   C21        1.0     0.426506      0.826122      0.551618     Biso  1.000000 C
   C22        1.0     0.061242      0.287455      0.556955     Biso  1.000000 C
   C23        1.0     0.158259      0.349585      0.460330     Biso  1.000000 C
   C24        1.0     0.099994      0.138562      0.602909     Biso  1.000000 C
   C25        1.0     0.293068      0.262513      0.405977     Biso  1.000000 C
   C26        1.0     0.240709      0.051779      0.556750     Biso  1.000000 C
   C27        1.0     0.336075      0.112868      0.446332     Biso  1.000000 C
   C28        1.0     0.289215      0.912825      0.607573     Biso  1.000000 C
   H1         1.0     0.328881      0.847007      0.150002     Biso  1.000000 H
   H2         1.0     0.464008      0.246700      0.786374     Biso  1.000000 H
   H3         1.0     0.256597      0.599057      0.250906     Biso  1.000000 H
   H4         1.0     0.180704      0.921418      0.936795     Biso  1.000000 H
   H5         1.0     0.946413      0.889846      0.780423     Biso  1.000000 H
   H6         1.0     0.035213      0.435953      0.147467     Biso  1.000000 H
   H7         1.0     0.622168      0.166956      0.990034     Biso  1.000000 H
   H8         1.0     0.540515      0.490738      0.678956     Biso  1.000000 H
   H9         1.0     0.721694      0.723199      0.673422     Biso  1.000000 H
   H10        1.0     0.854418      0.312302      0.072555     Biso  1.000000 H
   H11        1.0     0.842408      0.775102      0.221199     Biso  1.000000 H
   H12        1.0     0.963190      0.360829      0.606205     Biso  1.000000 H
   H13        1.0     0.754518      0.011553      0.114084     Biso  1.000000 H
   H14        1.0     0.697161      0.694501      0.435412     Biso  1.000000 H
   H15        1.0     0.455076      0.711419      0.586250     Biso  1.000000 H
   H16        1.0     0.523525      0.167037      0.218488     Biso  1.000000 H
   H17        1.0     0.130211      0.459584      0.419048     Biso  1.000000 H
   H18        1.0     0.036290      0.104707      0.696416     Biso  1.000000 H
   H19        1.0     0.222146      0.868650      0.693039     Biso  1.000000 H
   H20        1.0     0.366624      0.316211      0.332679     Biso  1.000000 H
   K1         1.0     0.042110      0.074333      0.232624     Biso  1.000000 K
   K2         1.0     0.735952      0.152823      0.566958     Biso  1.000000 K
   K3         1.0     0.242341      0.464780      0.801586     Biso  1.000000 K
   K4         1.0     0.541464      0.570971      0.137380     Biso  1.000000 K
   K5         1.0     0.014265      0.747870      0.476931     Biso  1.000000 K
   K6         1.0     0.515592      0.879690      0.883883     Biso  1.000000 K
```

### 2. Structure *EA2*

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_EA2


_pd_phase_name                         'EA376   9.874 10.123  9.642 113.457 90'
_cell_length_a                         9.43072
_cell_length_b                         9.88197
_cell_length_c                         9.30359
_cell_angle_alpha                      112.95712
_cell_angle_beta                       91.82224
_cell_angle_gamma                      98.41454
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.593349      0.322232      0.633825     Biso  1.000000 C
   C2         1.0     0.619814      0.179385      0.610941     Biso  1.000000 C
   C3         1.0     0.576455      0.362860      0.507546     Biso  1.000000 C
   C4         1.0     0.619213      0.073577      0.453311     Biso  1.000000 C
   C5         1.0     0.593044      0.263012      0.347730     Biso  1.000000 C
   C6         1.0     0.600691      0.108385      0.322594     Biso  1.000000 C
   C7         1.0     0.598036      0.306536      0.222096     Biso  1.000000 C
   C8         1.0     0.584097      0.784330      0.844042     Biso  1.000000 C
   C9         1.0     0.591501      0.736991      0.967879     Biso  1.000000 C
   C10        1.0     0.577304      0.932213      0.872624     Biso  1.000000 C
   C11        1.0     0.590464      0.844729      0.122744     Biso  1.000000 C
   C12        1.0     0.587054      0.047263      0.030257     Biso  1.000000 C
   C13        1.0     0.592111      0.996603      0.158627     Biso  1.000000 C
   C14        1.0     0.593137      0.198546      0.062658     Biso  1.000000 C
   C15        1.0     0.923135      0.790783      0.600508     Biso  1.000000 C
   C16        1.0     0.819650      0.727399      0.469794     Biso  1.000000 C
   C17        1.0     0.068571      0.783612      0.584141     Biso  1.000000 C
   C18        1.0     0.868938      0.654927      0.319429     Biso  1.000000 C
   C19        1.0     0.121857      0.708619      0.432794     Biso  1.000000 C
   C20        1.0     0.013519      0.644539      0.296276     Biso  1.000000 C
   C21        1.0     0.266191      0.696184      0.413892     Biso  1.000000 C
   C22        1.0     0.155296      0.407668      0.839435     Biso  1.000000 C
   C23        1.0     0.010326      0.425958      0.849979     Biso  1.000000 C
   C24        1.0     0.254255      0.467876      0.971836     Biso  1.000000 C
   C25        1.0     0.967179      0.505214      0.001333     Biso  1.000000 C
   C26        1.0     0.214710      0.554139      0.127199     Biso  1.000000 C
   C27        1.0     0.061690      0.566061      0.138509     Biso  1.000000 C
   C28        1.0     0.313113      0.621339      0.260595     Biso  1.000000 C
   H1         1.0     0.584842      0.403026      0.751999     Biso  1.000000 H
   H2         1.0     0.582287      0.703831      0.723173     Biso  1.000000 H
   H3         1.0     0.636165      0.148321      0.709551     Biso  1.000000 H
   H4         1.0     0.554434      0.474137      0.528113     Biso  1.000000 H
   H5         1.0     0.595389      0.423431      0.244908     Biso  1.000000 H
   H6         1.0     0.629981      0.959776      0.436328     Biso  1.000000 H
   H7         1.0     0.596769      0.621546      0.946389     Biso  1.000000 H
   H8         1.0     0.566603      0.964921      0.773787     Biso  1.000000 H
   H9         1.0     0.583554      0.233814      0.965319     Biso  1.000000 H
   H10        1.0     0.587515      0.806229      0.218040     Biso  1.000000 H
   H11        1.0     0.888685      0.841818      0.718263     Biso  1.000000 H
   H12        1.0     0.191271      0.346975      0.724560     Biso  1.000000 H
   H13        1.0     0.705388      0.728894      0.482788     Biso  1.000000 H
   H14        1.0     0.146079      0.832761      0.688773     Biso  1.000000 H
   H15        1.0     0.343916      0.738446      0.518119     Biso  1.000000 H
   H16        1.0     0.788390      0.602410      0.218057     Biso  1.000000 H
   H17        1.0     0.930571      0.374521      0.747868     Biso  1.000000 H
   H18        1.0     0.366823      0.454261      0.959659     Biso  1.000000 H
   H19        1.0     0.426654      0.611949      0.248734     Biso  1.000000 H
   H20        1.0     0.854352      0.518076      0.008976     Biso  1.000000 H
   K1         1.0     0.288439      0.302419      0.229998     Biso  1.000000 K
   K2         1.0     0.895456      0.943764      0.273912     Biso  1.000000 K
   K3         1.0     0.888073      0.164401      0.939299     Biso  1.000000 K
   K4         1.0     0.275117      0.779407      0.978011     Biso  1.000000 K
   K5         1.0     0.898250      0.445090      0.481604     Biso  1.000000 K
   K6         1.0     0.305167      0.035532      0.514921     Biso  1.000000 K
```

### 3. Structure *EA3(M)*

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_EA3M


_pd_phase_name                         'EA363  10.231  9.177  9.795 96.002 106'
_cell_length_a                         10.20131
_cell_length_b                         9.12298
_cell_length_c                         9.59360
_cell_angle_alpha                      97.24651
```

```
_cell_angle_beta                       107.84360
_cell_angle_gamma                      116.23448
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.836169     0.109741     0.105015     Biso  1.000000 C
   C2         1.0     0.834416     0.243207     0.046033     Biso  1.000000 C
   C3         1.0     0.746000     0.044297     0.191423     Biso  1.000000 C
   C4         1.0     0.735750     0.307443     0.071244     Biso  1.000000 C
   C5         1.0     0.646497     0.106824     0.220892     Biso  1.000000 C
   C6         1.0     0.633995     0.236727     0.147982     Biso  1.000000 C
   C7         1.0     0.561124     0.052875     0.312388     Biso  1.000000 C
   C8         1.0     0.297715     0.394569     0.174598     Biso  1.000000 C
   C9         1.0     0.372780     0.442383     0.073868     Biso  1.000000 C
   C10        1.0     0.318861     0.281037     0.254838     Biso  1.000000 C
   C11        1.0     0.470581     0.375044     0.054245     Biso  1.000000 C
   C12        1.0     0.427385     0.222690     0.248027     Biso  1.000000 C
   C13        1.0     0.507925     0.274398     0.143887     Biso  1.000000 C
   C14        1.0     0.463002     0.122565     0.336438     Biso  1.000000 C
   C15        1.0     0.344525     0.621126     0.613722     Biso  1.000000 C
   C16        1.0     0.329814     0.740943     0.540592     Biso  1.000000 C
   C17        1.0     0.256285     0.558847     0.702118     Biso  1.000000 C
   C18        1.0     0.222949     0.797038     0.556454     Biso  1.000000 C
   C19        1.0     0.149079     0.614115     0.723134     Biso  1.000000 C
   C20        1.0     0.129437     0.735750     0.642254     Biso  1.000000 C
   C21        1.0     0.065917     0.561480     0.816619     Biso  1.000000 C
   C22        1.0     0.780823     0.879139     0.663294     Biso  1.000000 C
   C23        1.0     0.873317     0.949807     0.581274     Biso  1.000000 C
   C24        1.0     0.800106     0.760620     0.737394     Biso  1.000000 C
   C25        1.0     0.981715     0.895235     0.568793     Biso  1.000000 C
   C26        1.0     0.922675     0.720091     0.743486     Biso  1.000000 C
   C27        1.0     0.010051     0.782195     0.646685     Biso  1.000000 C
   C28        1.0     0.963751     0.627004     0.837422     Biso  1.000000 C
   H1         1.0     0.909430     0.057127     0.087055     Biso  1.000000 H
   H2         1.0     0.217092     0.438509     0.188195     Biso  1.000000 H
   H3         1.0     0.911823     0.300989     0.987497     Biso  1.000000 H
   H4         1.0     0.750406     0.941652     0.236699     Biso  1.000000 H
   H5         1.0     0.571257     0.957965     0.367768     Biso  1.000000 H
   H6         1.0     0.735216     0.411721     0.026397     Biso  1.000000 H
   H7         1.0     0.352770     0.524115     0.006532     Biso  1.000000 H
   H8         1.0     0.260751     0.246370     0.333778     Biso  1.000000 H
   H9         1.0     0.400061     0.081364     0.411215     Biso  1.000000 H
   H10        1.0     0.526383     0.411418     0.973989     Biso  1.000000 H
   H11        1.0     0.426017     0.577094     0.604059     Biso  1.000000 H
   H12        1.0     0.689907     0.910349     0.667575     Biso  1.000000 H
   H13        1.0     0.403878     0.794981     0.478233     Biso  1.000000 H
   H14        1.0     0.269122     0.465385     0.757293     Biso  1.000000 H
   H15        1.0     0.082444     0.472639     0.877286     Biso  1.000000 H
   H16        1.0     0.213492     0.891304     0.500615     Biso  1.000000 H
   H17        1.0     0.856440     0.036942     0.519337     Biso  1.000000 H
   H18        1.0     0.730930     0.710835     0.804949     Biso  1.000000 H
   H19        1.0     0.896508     0.580708     0.907857     Biso  1.000000 H
   H20        1.0     0.049128     0.948377     0.500941     Biso  1.000000 H
   K1         1.0     0.219902     0.766625     0.154599     Biso  1.000000 K
   K2         1.0     0.651793     0.599920     0.378940     Biso  1.000000 K
   K3         1.0     0.718098     0.282018     0.649843     Biso  1.000000 K
   K4         1.0     0.486870     0.931263     0.880648     Biso  1.000000 K
   K5         1.0     0.122075     0.088187     0.904903     Biso  1.000000 K
   K6         1.0     0.996509     0.406150     0.389058     Biso  1.000000 K
```

## 4. *Structure* ***EA3(SM)***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_EA3SM


_pd_phase_name                         'EA1363  9.952  8.912  9.476 95.049 114'
_cell_length_a                         9.96513
_cell_length_b                         8.92428
_cell_length_c                         9.48859
_cell_angle_alpha                      95.07159
_cell_angle_beta                       114.24680
_cell_angle_gamma                      64.96310
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.188870     0.490867     0.617449     Biso  1.000000 C
   C2         1.0     0.200130     0.630211     0.572191     Biso  1.000000 C
   C3         1.0     0.099609     0.507258     0.705628     Biso  1.000000 C
   C4         1.0     0.113623     0.790365     0.612481     Biso  1.000000 C
   C5         1.0     0.009944     0.666282     0.747380     Biso  1.000000 C
   C6         1.0     0.008819     0.814873     0.687234     Biso  1.000000 C
   C7         1.0     0.922491     0.689236     0.837597     Biso  1.000000 C
   C8         1.0     0.707270     0.306014     0.756389     Biso  1.000000 C
   C9         1.0     0.773794     0.289074     0.647278     Biso  1.000000 C
   C10        1.0     0.720710     0.164395     0.827448     Biso  1.000000 C
   C11        1.0     0.859100     0.126408     0.613167     Biso  1.000000 C
   C12        1.0     0.812035     0.998054     0.801361     Biso  1.000000 C
   C13        1.0     0.889388     0.979432     0.693220     Biso  1.000000 C
   C14        1.0     0.834865     0.853763     0.875005     Biso  1.000000 C
   C15        1.0     0.722862     0.492121     0.151052     Biso  1.000000 C
   C16        1.0     0.694191     0.631062     0.064311     Biso  1.000000 C
   C17        1.0     0.635820     0.510467     0.241913     Biso  1.000000 C
   C18        1.0     0.577082     0.791924     0.071942     Biso  1.000000 C
   C19        1.0     0.522097     0.670823     0.258024     Biso  1.000000 C
   C20        1.0     0.496798     0.818160     0.172331     Biso  1.000000 C
   C21        1.0     0.438289     0.694419     0.352120     Biso  1.000000 C
   C22        1.0     0.166688     0.309117     0.214225     Biso  1.000000 C
   C23        1.0     0.269345     0.294044     0.141387     Biso  1.000000 C
   C24        1.0     0.184732     0.167341     0.288923     Biso  1.000000 C
   C25        1.0     0.386809     0.132244     0.138699     Biso  1.000000 C
   C26        1.0     0.301140     0.002229     0.288186     Biso  1.000000 C
   C27        1.0     0.400164     0.984596     0.201381     Biso  1.000000 C
   C28        1.0     0.323202     0.859139     0.362391     Biso  1.000000 C
   H1         1.0     0.248359     0.367999     0.584192     Biso  1.000000 H
   H2         1.0     0.646316     0.428107     0.790190     Biso  1.000000 H
   H3         1.0     0.281099     0.614903     0.516386     Biso  1.000000 H
   H4         1.0     0.091083     0.397785     0.737424     Biso  1.000000 H
   H5         1.0     0.925866     0.578693     0.884020     Biso  1.000000 H
   H6         1.0     0.119290     0.899106     0.574889     Biso  1.000000 H
   H7         1.0     0.761475     0.397249     0.588944     Biso  1.000000 H
   H8         1.0     0.670542     0.179496     0.913754     Biso  1.000000 H
   H9         1.0     0.775669     0.868142     0.953792     Biso  1.000000 H
   H10        1.0     0.911561     0.114718     0.529504     Biso  1.000000 H
   H11        1.0     0.812182     0.368802     0.147367     Biso  1.000000 H
   H12        1.0     0.067110     0.428003     0.210372     Biso  1.000000 H
   H13        1.0     0.764121     0.615999     0.996470     Biso  1.000000 H
   H14        1.0     0.659632     0.400959     0.308117     Biso  1.000000 H
   H15        1.0     0.459563     0.584298     0.416322     Biso  1.000000 H
   H16        1.0     0.558615     0.900147     0.008019     Biso  1.000000 H
   H17        1.0     0.252569     0.400247     0.076164     Biso  1.000000 H
   H18        1.0     0.104978     0.181809     0.346102     Biso  1.000000 H
   H19        1.0     0.248747     0.873786     0.426008     Biso  1.000000 H
   H20        1.0     0.463124     0.122371     0.079128     Biso  1.000000 H
   K1         1.0     0.569192     0.755658     0.687538     Biso  1.000000 K
   K2         1.0     0.375475     0.587892     0.921694     Biso  1.000000 K
   K3         1.0     0.506275     0.189168     0.476439     Biso  1.000000 K
   K4         1.0     0.107961     0.703157     0.180947     Biso  1.000000 K
   K5         1.0     0.070403     0.125132     0.941596     Biso  1.000000 K
   K6         1.0     0.838530     0.696998     0.402140     Biso  1.000000 K
```

## 5. *Structure* ***PS–$K_3$Phenanthrene***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_PS_K3PA


_pd_phase_name                         'Structure from PWSCF output 17438TITLE'
_cell_length_a                         9.17265
_cell_length_b                         6.51744
_cell_length_c                         10.35332
_cell_angle_alpha                      90
_cell_angle_beta                       102.60990
_cell_angle_gamma                      90
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.750724     0.105397     0.250145     Biso  1.000000 C
   C2         1.0     0.249276     0.605397     0.749855     Biso  1.000000 C
   C3         1.0     0.884977     0.013301     0.323302     Biso  1.000000 C
   C4         1.0     0.115023     0.513301     0.676698     Biso  1.000000 C
   C5         1.0     0.973827     0.897250     0.257254     Biso  1.000000 C
   C6         1.0     0.026173     0.397250     0.742746     Biso  1.000000 C
   C7         1.0     0.928428     0.870674     0.117023     Biso  1.000000 C
   C8         1.0     0.071572     0.370674     0.882976     Biso  1.000000 C
   C9         1.0     0.848052     0.851466     0.818369     Biso  1.000000 C
   C10        1.0     0.151948     0.351466     0.181631     Biso  1.000000 C
   C11        1.0     0.817825     0.860547     0.677282     Biso  1.000000 C
   C12        1.0     0.182175     0.360547     0.322718     Biso  1.000000 C
   C13        1.0     0.688699     0.959540     0.607544     Biso  1.000000 C
   C14        1.0     0.311301     0.459540     0.392456     Biso  1.000000 C
   C15        1.0     0.588481     0.049775     0.678163     Biso  1.000000 C
   C16        1.0     0.411519     0.549775     0.321837     Biso  1.000000 C
```

```
C17         1.0     0.535092      0.170798      0.893078     Biso  1.000000 C
C18         1.0     0.464909      0.670798      0.106922     Biso  1.000000 C
C19         1.0     0.571244      0.175743      0.035624     Biso  1.000000 C
C20         1.0     0.428756      0.675743      0.964376     Biso  1.000000 C
C21         1.0     0.702215      0.084919      0.108800     Biso  1.000000 C
C22         1.0     0.297785      0.584919      0.891200     Biso  1.000000 C
C23         1.0     0.798121      0.967964      0.038260     Biso  1.000000 C
C24         1.0     0.201879      0.467964      0.961740     Biso  1.000000 C
C25         1.0     0.758046      0.955764      0.894669     Biso  1.000000 C
C26         1.0     0.241954      0.455764      0.105330     Biso  1.000000 C
C27         1.0     0.622781      0.062147      0.820924     Biso  1.000000 C
C28         1.0     0.377219      0.562147      0.179076     Biso  1.000000 C
H1          1.0     0.681901      0.197403      0.302743     Biso  1.000000 H
H2          1.0     0.318099      0.697403      0.697257     Biso  1.000000 H
H3          1.0     0.913669      0.032517      0.431032     Biso  1.000000 H
H4          1.0     0.086331      0.532517      0.568968     Biso  1.000000 H
H5          1.0     0.076771      0.823467      0.310402     Biso  1.000000 H
H6          1.0     0.923229      0.323467      0.689598     Biso  1.000000 H
H7          1.0     0.000830      0.777365      0.069427     Biso  1.000000 H
H8          1.0     0.999170      0.277365      0.930573     Biso  1.000000 H
H9          1.0     0.949378      0.770712      0.867420     Biso  1.000000 H
H10         1.0     0.050622      0.270713      0.132580     Biso  1.000000 H
H11         1.0     0.894871      0.784578      0.625862     Biso  1.000000 H
H12         1.0     0.105129      0.284578      0.374138     Biso  1.000000 H
H13         1.0     0.668494      0.967945      0.499535     Biso  1.000000 H
H14         1.0     0.331506      0.467945      0.500465     Biso  1.000000 H
H15         1.0     0.488337      0.129799      0.623469     Biso  1.000000 H
H16         1.0     0.511663      0.629799      0.376531     Biso  1.000000 H
H17         1.0     0.435468      0.253438      0.840658     Biso  1.000000 H
H18         1.0     0.564532      0.753438      0.159342     Biso  1.000000 H
H19         1.0     0.508199      0.280162      0.085588     Biso  1.000000 H
H20         1.0     0.491801      0.780162      0.914412     Biso  1.000000 H
K1          1.0     0.833687      0.553203      0.354523     Biso  1.000000 K
K2          1.0     0.166313      0.053203      0.645477     Biso  1.000000 K
K3          1.0     0.770137      0.495779      0.002727     Biso  1.000000 K
K4          1.0     0.229863      0.995779      0.997273     Biso  1.000000 K
K5          1.0     0.582063      0.548047      0.691408     Biso  1.000000 K
K6          1.0     0.417937      0.048047      0.308593     Biso  1.000000 K
```

## B. $K_3$-picene

### 1. *Structure* ***A***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_A


_pd_phase_name                         'EA277  10.292  7.529 12.847 76.857 90.'
_cell_length_a                         10.01017
_cell_length_b                         7.32203
_cell_length_c                         12.67017
_cell_angle_alpha                      77.62717
_cell_angle_beta                       90.21521
_cell_angle_gamma                      90.24959
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1          1.0     0.043654      0.976564      0.361841     Biso  1.000000 C
   C2          1.0     0.081781      0.877539      0.282139     Biso  1.000000 C
   C3          1.0     0.078243      0.912305      0.473544     Biso  1.000000 C
   C4          1.0     0.141312      0.692073      0.316783     Biso  1.000000 C
   C5          1.0     0.069358      0.954650      0.166345     Biso  1.000000 C
   C6          1.0     0.174209      0.629734      0.429822     Biso  1.000000 C
   C7          1.0     0.163292      0.585507      0.237452     Biso  1.000000 C
   C8          1.0     0.146225      0.742327      0.505583     Biso  1.000000 C
   C9          1.0     0.067339      0.828101      0.090218     Biso  1.000000 C
   C10         1.0     0.118259      0.647956      0.128066     Biso  1.000000 C
   C11         1.0     0.017623      0.900508      0.979890     Biso  1.000000 C
   C12         1.0     0.051659      0.147592      0.124559     Biso  1.000000 C
   C13         1.0     0.008390      0.217869      0.018269     Biso  1.000000 C
   C14         1.0     0.981342      0.096498      0.946359     Biso  1.000000 C
   C15         1.0     0.921403      0.164994      0.841494     Biso  1.000000 C
   C16         1.0     0.005607      0.787369      0.903359     Biso  1.000000 C
   C17         1.0     0.908775      0.040478      0.766241     Biso  1.000000 C
   C18         1.0     0.955701      0.854826      0.798730     Biso  1.000000 C
   C19         1.0     0.848008      0.109476      0.662896     Biso  1.000000 C
   C20         1.0     0.871068      0.352253      0.807458     Biso  1.000000 C
   C21         1.0     0.811134      0.415877      0.704647     Biso  1.000000 C
   C22         1.0     0.799886      0.294420      0.632570     Biso  1.000000 C
   C23         1.0     0.543177      0.512665      0.140261     Biso  1.000000 C
   C24         1.0     0.581939      0.611490      0.220209     Biso  1.000000 C
   C25         1.0     0.577626      0.577539      0.028688     Biso  1.000000 C
   C26         1.0     0.641963      0.797226      0.186134     Biso  1.000000 C
   C27         1.0     0.569073      0.534004      0.335984     Biso  1.000000 C
   C28         1.0     0.675657      0.859541      0.073334     Biso  1.000000 C
   C29         1.0     0.663216      0.904213      0.265506     Biso  1.000000 C
   C30         1.0     0.646763      0.747390      0.997320     Biso  1.000000 C
   C31         1.0     0.567177      0.660418      0.412108     Biso  1.000000 C
   C32         1.0     0.618061      0.841165      0.374652     Biso  1.000000 C
   C33         1.0     0.517561      0.587139      0.522280     Biso  1.000000 C
   C34         1.0     0.551172      0.341009      0.377371     Biso  1.000000 C
   C35         1.0     0.507594      0.269999      0.483380     Biso  1.000000 C
   C36         1.0     0.480885      0.390907      0.555290     Biso  1.000000 C
   C37         1.0     0.420937      0.321573      0.659868     Biso  1.000000 C
   C38         1.0     0.506096      0.699626      0.599043     Biso  1.000000 C
   C39         1.0     0.409193      0.445347      0.735498     Biso  1.000000 C
   C40         1.0     0.456505      0.631289      0.703492     Biso  1.000000 C
   C41         1.0     0.348640      0.375104      0.838624     Biso  1.000000 C
   C42         1.0     0.369861      0.134179      0.693136     Biso  1.000000 C
   C43         1.0     0.310013      0.069443      0.795611     Biso  1.000000 C
   C44         1.0     0.299652      0.190155      0.868119     Biso  1.000000 C
   H1          1.0     0.990681      0.109126      0.337002     Biso  1.000000 H
   H2          1.0     0.053060      0.995470      0.532408     Biso  1.000000 H
   H3          1.0     0.234078      0.502795      0.453402     Biso  1.000000 H
   H4          1.0     0.209082      0.447498      0.262070     Biso  1.000000 H
   H5          1.0     0.183762      0.702932      0.588538     Biso  1.000000 H
   H6          1.0     0.131076      0.552972      0.073021     Biso  1.000000 H
   H7          1.0     0.073601      0.244154      0.177459     Biso  1.000000 H
   H8          1.0     0.008935      0.368109      0.985571     Biso  1.000000 H
   H9          1.0     0.039392      0.642720      0.923935     Biso  1.000000 H
   H10         1.0     0.948486      0.761894      0.742098     Biso  1.000000 H
   H11         1.0     0.836106      0.014331      0.607825     Biso  1.000000 H
   H12         1.0     0.873084      0.446962      0.863002     Biso  1.000000 H
   H13         1.0     0.767248      0.555438      0.684253     Biso  1.000000 H
   H14         1.0     0.744649      0.335233      0.556945     Biso  1.000000 H
   H15         1.0     0.489432      0.380186      0.164712     Biso  1.000000 H
   H16         1.0     0.551735      0.494776      0.969516     Biso  1.000000 H
   H17         1.0     0.736135      0.986560      0.050115     Biso  1.000000 H
   H18         1.0     0.709049      0.042698      0.241228     Biso  1.000000 H
   H19         1.0     0.684643      0.786849      0.914642     Biso  1.000000 H
   H20         1.0     0.630755      0.936242      0.429788     Biso  1.000000 H
   H21         1.0     0.573030      0.244887      0.324400     Biso  1.000000 H
   H22         1.0     0.507933      0.119773      0.516023     Biso  1.000000 H
   H23         1.0     0.540157      0.844580      0.578801     Biso  1.000000 H
   H24         1.0     0.449694      0.723902      0.760291     Biso  1.000000 H
   H25         1.0     0.337260      0.469618      0.894015     Biso  1.000000 H
   H26         1.0     0.371010      0.040292      0.637102     Biso  1.000000 H
   H27         1.0     0.265521      0.929804      0.815439     Biso  1.000000 H
```

```
   H28        1.0     0.244365      0.148477      0.943427     Biso  1.000000 H
   K1         1.0     0.366052      0.853274      0.080021     Biso  1.000000 K
   K2         1.0     0.865147      0.636019      0.422516     Biso  1.000000 K
   K3         1.0     0.613925      0.141035      0.831662     Biso  1.000000 K
   K4         1.0     0.113814      0.345484      0.669154     Biso  1.000000 K
   K5         1.0     0.847151      0.495566      0.129264     Biso  1.000000 K
   K6         1.0     0.347314      0.991941      0.372045     Biso  1.000000 K
```

## 2. *Structure* ***B***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_B


_pd_phase_name                         'EA334  10.672  7.649 14.575 91.235 105'
_cell_length_a                         9.83379
_cell_length_b                         6.91916
_cell_length_c                         13.86159
_cell_angle_alpha                      86.02428
_cell_angle_beta                       100.67679
_cell_angle_gamma                      78.55915
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.552595      0.880908      0.168771     Biso  1.000000 C
   C2         1.0     0.473584      0.737718      0.131609     Biso  1.000000 C
   C3         1.0     0.600430      0.885843      0.271189     Biso  1.000000 C
   C4         1.0     0.457112      0.585304      0.204640     Biso  1.000000 C
   C5         1.0     0.414016      0.734769      0.028593     Biso  1.000000 C
   C6         1.0     0.500963      0.599711      0.307125     Biso  1.000000 C
   C7         1.0     0.403653      0.421083      0.168787     Biso  1.000000 C
   C8         1.0     0.573260      0.749724      0.341199     Biso  1.000000 C
   C9         1.0     0.349410      0.567716      0.995093     Biso  1.000000 C
   C10        1.0     0.351769      0.414275      0.068532     Biso  1.000000 C
   C11        1.0     0.296296      0.560712      0.890712     Biso  1.000000 C
   C12        1.0     0.423701      0.881770      0.953227     Biso  1.000000 C
   C13        1.0     0.377486      0.870766      0.852644     Biso  1.000000 C
   C14        1.0     0.312782      0.713113      0.816287     Biso  1.000000 C
   C15        1.0     0.270559      0.696862      0.712782     Biso  1.000000 C
   C16        1.0     0.233012      0.406125      0.854465     Biso  1.000000 C
   C17        1.0     0.192755      0.544446      0.680282     Biso  1.000000 C
   C18        1.0     0.180969      0.398783      0.754451     Biso  1.000000 C
   C19        1.0     0.142772      0.537078      0.577919     Biso  1.000000 C
   C20        1.0     0.306503      0.817543      0.635841     Biso  1.000000 C
   C21        1.0     0.263572      0.796468      0.534952     Biso  1.000000 C
   C22        1.0     0.179120      0.660866      0.504242     Biso  1.000000 C
   C23        1.0     0.695282      0.986673      0.682902     Biso  1.000000 C
   C24        1.0     0.753680      0.148604      0.720077     Biso  1.000000 C
   C25        1.0     0.644108      0.982125      0.580914     Biso  1.000000 C
   C26        1.0     0.763072      0.304956      0.646581     Biso  1.000000 C
   C27        1.0     0.796466      0.167512      0.823638     Biso  1.000000 C
   C28        1.0     0.716558      0.291041      0.544214     Biso  1.000000 C
   C29        1.0     0.813168      0.472219      0.681519     Biso  1.000000 C
   C30        1.0     0.653726      0.132028      0.510649     Biso  1.000000 C
   C31        1.0     0.867384      0.329376      0.855858     Biso  1.000000 C
   C32        1.0     0.868026      0.479001      0.781286     Biso  1.000000 C
   C33        1.0     0.919241      0.339281      0.959941     Biso  1.000000 C
   C34        1.0     0.770680      0.037106      0.900116     Biso  1.000000 C
   C35        1.0     0.817797      0.049011      0.000275     Biso  1.000000 C
   C36        1.0     0.899150      0.191909      0.035365     Biso  1.000000 C
   C37        1.0     0.957127      0.196181      0.137999     Biso  1.000000 C
   C38        1.0     0.981297      0.495859      0.995345     Biso  1.000000 C
   C39        1.0     0.028260      0.356152      0.169400     Biso  1.000000 C
   C40        1.0     0.032023      0.506669      0.094861     Biso  1.000000 C
   C41        1.0     0.082823      0.363170      0.271056     Biso  1.000000 C
   C42        1.0     0.943665      0.055374      0.216192     Biso  1.000000 C
   C43        1.0     0.992869      0.073314      0.316678     Biso  1.000000 C
   C44        1.0     0.063461      0.224852      0.346005     Biso  1.000000 C
   H1         1.0     0.574969      0.991451      0.117594     Biso  1.000000 H
   H2         1.0     0.661264      0.996092      0.295348     Biso  1.000000 H
   H3         1.0     0.484638      0.486072      0.359946     Biso  1.000000 H
   H4         1.0     0.402734      0.299343      0.222996     Biso  1.000000 H
   H5         1.0     0.611890      0.753147      0.419807     Biso  1.000000 H
   H6         1.0     0.312936      0.283385      0.046685     Biso  1.000000 H
   H7         1.0     0.469269      0.007950      0.974472     Biso  1.000000 H
   H8         1.0     0.386046      0.991418      0.800742     Biso  1.000000 H
   H9         1.0     0.221362      0.289104      0.906883     Biso  1.000000 H
   H10        1.0     0.129318      0.278783      0.731088     Biso  1.000000 H
   H11        1.0     0.081516      0.425748      0.555832     Biso  1.000000 H
   H12        1.0     0.377427      0.917373      0.656328     Biso  1.000000 H
   H13        1.0     0.298304      0.886988      0.480427     Biso  1.000000 H
   H14        1.0     0.143053      0.648800      0.426132     Biso  1.000000 H
   H15        1.0     0.686472      0.865319      0.734051     Biso  1.000000 H
   H16        1.0     0.595271      0.859835      0.557754     Biso  1.000000 H
   H17        1.0     0.722616      0.412321      0.491457     Biso  1.000000 H
   H18        1.0     0.815905      0.592410      0.627330     Biso  1.000000 H
   H19        1.0     0.612400      0.128879      0.432261     Biso  1.000000 H
   H20        1.0     0.910507      0.607859      0.801434     Biso  1.000000 H
   H21        1.0     0.707884      0.927106      0.879647     Biso  1.000000 H
   H22        1.0     0.791554      0.945734      0.053207     Biso  1.000000 H
   H23        1.0     0.990579      0.612268      0.941539     Biso  1.000000 H
   H24        1.0     0.079687      0.630307      0.118022     Biso  1.000000 H
   H25        1.0     0.136649      0.482800      0.291569     Biso  1.000000 H
   H26        1.0     0.889524      0.935718      0.197671     Biso  1.000000 H
   H27        1.0     0.977369      0.964024      0.371980     Biso  1.000000 H
   H28        1.0     0.105677      0.233974      0.423716     Biso  1.000000 H
   K1         1.0     0.273239      0.975336      0.245553     Biso  1.000000 K
   K2         1.0     0.768464      0.470129      0.243626     Biso  1.000000 K
   K3         1.0     0.611149      0.480424      0.921872     Biso  1.000000 K
   K4         1.0     0.100064      0.940449      0.928312     Biso  1.000000 K
   K5         1.0     0.970566      0.946548      0.592755     Biso  1.000000 K
   K6         1.0     0.449855      0.360329      0.621226     Biso  1.000000 K
```

## 3. *Structure* ***C***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_C


_pd_phase_name                         'EA188   7.932  7.540 13.623 97.445 89.'
_cell_length_a                         7.93912
_cell_length_b                         7.55680
_cell_length_c                         13.65582
_cell_angle_alpha                      97.43658
_cell_angle_beta                       89.93323
_cell_angle_gamma                      90.02206
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.576489      0.657849      0.595051     Biso  1.000000 C
   C2         1.0     0.459376      0.715317      0.528319     Biso  1.000000 C
   C3         1.0     0.684022      0.514905      0.564808     Biso  1.000000 C
   C4         1.0     0.450372      0.633778      0.427577     Biso  1.000000 C
   C5         1.0     0.676938      0.430540      0.465591     Biso  1.000000 C
   C6         1.0     0.563897      0.485830      0.394806     Biso  1.000000 C
   C7         1.0     0.340178      0.696032      0.358088     Biso  1.000000 C
   C8         1.0     0.561066      0.404926      0.290909     Biso  1.000000 C
   C9         1.0     0.337059      0.614361      0.258149     Biso  1.000000 C
   C10        1.0     0.442908      0.473180      0.221852     Biso  1.000000 C
   C11        1.0     0.673859      0.268407      0.252602     Biso  1.000000 C
   C12        1.0     0.443740      0.396212      0.115872     Biso  1.000000 C
   C13        1.0     0.679198      0.200211      0.150556     Biso  1.000000 C
   C14        1.0     0.564513      0.255002      0.081313     Biso  1.000000 C
   C15        1.0     0.336591      0.458499      0.046588     Biso  1.000000 C
   C16        1.0     0.567367      0.180169      0.976436     Biso  1.000000 C
   C17        1.0     0.343995      0.392719      0.944076     Biso  1.000000 C
   C18        1.0     0.675806      0.038310      0.937540     Biso  1.000000 C
   C19        1.0     0.460023      0.258767      0.906976     Biso  1.000000 C
   C20        1.0     0.698893      0.990447      0.833583     Biso  1.000000 C
   C21        1.0     0.481638      0.203158      0.802941     Biso  1.000000 C
   C22        1.0     0.602461      0.074934      0.767352     Biso  1.000000 C
   C23        1.0     0.081111      0.595351      0.742062     Biso  1.000000 C
   C24        1.0     0.963088      0.537403      0.808277     Biso  1.000000 C
   C25        1.0     0.188704      0.737923      0.772899     Biso  1.000000 C
   C26        1.0     0.953210      0.617848      0.909228     Biso  1.000000 C
   C27        1.0     0.180622      0.821248      0.872301     Biso  1.000000 C
   C28        1.0     0.066502      0.765640      0.942487     Biso  1.000000 C
   C29        1.0     0.842280      0.554983      0.978279     Biso  1.000000 C
   C30        1.0     0.062183      0.846589      0.046383     Biso  1.000000 C
   C31        1.0     0.838539      0.635790      0.078406     Biso  1.000000 C
   C32        1.0     0.943876      0.777179      0.115060     Biso  1.000000 C
   C33        1.0     0.173905      0.983825      0.084856     Biso  1.000000 C
   C34        1.0     0.943795      0.853642      0.221104     Biso  1.000000 C
   C35        1.0     0.178848      0.050998      0.187021     Biso  1.000000 C
   C36        1.0     0.063983      0.994998      0.255970     Biso  1.000000 C
   C37        1.0     0.836356      0.790335      0.290110     Biso  1.000000 C
   C38        1.0     0.066458      0.068779      0.360992     Biso  1.000000 C
   C39        1.0     0.843019      0.855477      0.392678     Biso  1.000000 C
   C40        1.0     0.175517      0.209734      0.400293     Biso  1.000000 C
   C41        1.0     0.958610      0.989578      0.430063     Biso  1.000000 C
   C42        1.0     0.198193      0.256449      0.504330     Biso  1.000000 C
   C43        1.0     0.979375      0.044550      0.534169     Biso  1.000000 C
   C44        1.0     0.100486      0.172020      0.570156     Biso  1.000000 C
   H1         1.0     0.587479      0.733203      0.668356     Biso  1.000000 H
   H2         1.0     0.375724      0.828039      0.553226     Biso  1.000000 H
   H3         1.0     0.772037      0.466263      0.616706     Biso  1.000000 H
   H4         1.0     0.767949      0.324133      0.443663     Biso  1.000000 H
   H5         1.0     0.257104      0.809641      0.379862     Biso  1.000000 H
   H6         1.0     0.250908      0.673092      0.208955     Biso  1.000000 H
   H7         1.0     0.768532      0.218367      0.300258     Biso  1.000000 H
   H8         1.0     0.776693      0.101789      0.126847     Biso  1.000000 H
   H9         1.0     0.246311      0.565451      0.068522     Biso  1.000000 H
   H10        1.0     0.262572      0.452393      0.892769     Biso  1.000000 H
   H11        1.0     0.755562      0.972591      0.987199     Biso  1.000000 H
   H12        1.0     0.793350      0.890157      0.806544     Biso  1.000000 H
   H13        1.0     0.403447      0.264701      0.750488     Biso  1.000000 H
```

```
   H14        1.0     0.620422      0.041172      0.687759     Biso  1.000000 H
   H15        1.0     0.092556      0.520808      0.668540     Biso  1.000000 H
   H16        1.0     0.878938      0.425531      0.782733     Biso  1.000000 H
   H17        1.0     0.277244      0.787151      0.721416     Biso  1.000000 H
   H18        1.0     0.271302      0.927730      0.894763     Biso  1.000000 H
   H19        1.0     0.759342      0.441358      0.956243     Biso  1.000000 H
   H20        1.0     0.752188      0.576468      0.127365     Biso  1.000000 H
   H21        1.0     0.268047      0.035282      0.037284     Biso  1.000000 H
   H22        1.0     0.275885      0.149754      0.210990     Biso  1.000000 H
   H23        1.0     0.746530      0.683086      0.267856     Biso  1.000000 H
   H24        1.0     0.761337      0.795423      0.443837     Biso  1.000000 H
   H25        1.0     0.255738      0.275725      0.350865     Biso  1.000000 H
   H26        1.0     0.293096      0.355889      0.531770     Biso  1.000000 H
   H27        1.0     0.900278      0.982765      0.586210     Biso  1.000000 H
   H28        1.0     0.117928      0.205148      0.649812     Biso  1.000000 H
   K1         1.0     0.521894      0.844904      0.133478     Biso  1.000000 K
   K2         1.0     0.022109      0.404647      0.202560     Biso  1.000000 K
   K3         1.0     0.050181      0.620362      0.494791     Biso  1.000000 K
   K4         1.0     0.525553      0.061692      0.424774     Biso  1.000000 K
   K5         1.0     0.551396      0.626266      0.841003     Biso  1.000000 K
   K6         1.0     0.025080      0.187929      0.910496     Biso  1.000000 K
```

## 4. *Structure* ***D***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_D


_pd_phase_name                         'EA425   7.712  7.595 14.392 75.284 91.'
_cell_length_a                         7.72022
_cell_length_b                         7.60670
_cell_length_c                         14.42992
_cell_angle_alpha                      75.33833
_cell_angle_beta                       91.81866
_cell_angle_gamma                      90.08340
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.353113      0.790504      0.595693     Biso  1.000000 C
   C2         1.0     0.242176      0.862362      0.653863     Biso  1.000000 C
   C3         1.0     0.351241      0.855667      0.493509     Biso  1.000000 C
   C4         1.0     0.125018      0.010172      0.606357     Biso  1.000000 C
   C5         1.0     0.244709      0.797781      0.758797     Biso  1.000000 C
   C6         1.0     0.126201      0.073727      0.503548     Biso  1.000000 C
   C7         1.0     0.018434      0.088759      0.663009     Biso  1.000000 C
   C8         1.0     0.238373      0.997420      0.448767     Biso  1.000000 C
   C9         1.0     0.131091      0.883361      0.814426     Biso  1.000000 C
   C10        1.0     0.022349      0.025094      0.764836     Biso  1.000000 C
   C11        1.0     0.138295      0.821532      0.920882     Biso  1.000000 C
   C12        1.0     0.359086      0.659200      0.809370     Biso  1.000000 C
   C13        1.0     0.367373      0.601824      0.910994     Biso  1.000000 C
   C14        1.0     0.259199      0.676370      0.968693     Biso  1.000000 C
   C15        1.0     0.270318      0.617560      0.073846     Biso  1.000000 C
   C16        1.0     0.036410      0.901415      0.977752     Biso  1.000000 C
   C17        1.0     0.161137      0.706511      0.129143     Biso  1.000000 C
   C18        1.0     0.046339      0.845606      0.079742     Biso  1.000000 C
   C19        1.0     0.178141      0.653156      0.232227     Biso  1.000000 C
   C20        1.0     0.387481      0.480870      0.124898     Biso  1.000000 C
   C21        1.0     0.402905      0.431332      0.227498     Biso  1.000000 C
   C22        1.0     0.298385      0.518718      0.279595     Biso  1.000000 C
   C23        1.0     0.889658      0.284360      0.132089     Biso  1.000000 C
   C24        1.0     0.770607      0.212024      0.074831     Biso  1.000000 C
   C25        1.0     0.902176      0.219273      0.234107     Biso  1.000000 C
   C26        1.0     0.659945      0.063601      0.122897     Biso  1.000000 C
   C27        1.0     0.759736      0.276127      0.969960     Biso  1.000000 C
   C28        1.0     0.675176      0.000403      0.225768     Biso  1.000000 C
   C29        1.0     0.546751      0.983814      0.066635     Biso  1.000000 C
   C30        1.0     0.795342      0.077107      0.279710     Biso  1.000000 C
   C31        1.0     0.638878      0.190392      0.914757     Biso  1.000000 C
   C32        1.0     0.536723      0.047966      0.964774     Biso  1.000000 C
   C33        1.0     0.632703      0.252795      0.808286     Biso  1.000000 C
   C34        1.0     0.868668      0.414471      0.919472     Biso  1.000000 C
   C35        1.0     0.864505      0.471856      0.818036     Biso  1.000000 C
   C36        1.0     0.748517      0.398024      0.760635     Biso  1.000000 C
   C37        1.0     0.747481      0.457777      0.655663     Biso  1.000000 C
   C38        1.0     0.523908      0.173647      0.751072     Biso  1.000000 C
   C39        1.0     0.631920      0.369576      0.599926     Biso  1.000000 C
   C40        1.0     0.521947      0.230463      0.649033     Biso  1.000000 C
   C41        1.0     0.637983      0.424445      0.496979     Biso  1.000000 C
   C42        1.0     0.859508      0.594661      0.605447     Biso  1.000000 C
   C43        1.0     0.862859      0.646710      0.502971     Biso  1.000000 C
   C44        1.0     0.751594      0.561165      0.450200     Biso  1.000000 C
   H1         1.0     0.445516      0.682716      0.629315     Biso  1.000000 H
   H2         1.0     0.437818      0.794814      0.451441     Biso  1.000000 H
   H3         1.0     0.037865      0.184510      0.467045     Biso  1.000000 H
   H4         1.0     0.932881      0.202920      0.629462     Biso  1.000000 H
   H5         1.0     0.236196      0.051794      0.371194     Biso  1.000000 H
   H6         1.0     0.937351      0.095527      0.802828     Biso  1.000000 H
   H7         1.0     0.447386      0.593609      0.770523     Biso  1.000000 H
   H8         1.0     0.462336      0.496481      0.944239     Biso  1.000000 H
   H9         1.0     0.946028      0.012004      0.945935     Biso  1.000000 H
   H10        1.0     0.965577      0.916357      0.119821     Biso  1.000000 H
   H11        1.0     0.096415      0.719953      0.274310     Biso  1.000000 H
   H12        1.0     0.472311      0.412639      0.085577     Biso  1.000000 H
   H13        1.0     0.496714      0.327119      0.264242     Biso  1.000000 H
   H14        1.0     0.311010      0.483002      0.357703     Biso  1.000000 H
   H15        1.0     0.978079      0.391881      0.097841     Biso  1.000000 H
   H16        1.0     0.994978      0.280479      0.275341     Biso  1.000000 H
   H17        1.0     0.592462      0.888688      0.262850     Biso  1.000000 H
   H18        1.0     0.466066      0.868750      0.100445     Biso  1.000000 H
   H19        1.0     0.808257      0.021449      0.357135     Biso  1.000000 H
   H20        1.0     0.446578      0.977279      0.927117     Biso  1.000000 H
   H21        1.0     0.962599      0.479151      0.958208     Biso  1.000000 H
   H22        1.0     0.956150      0.576710      0.784755     Biso  1.000000 H
   H23        1.0     0.437143      0.062617      0.782587     Biso  1.000000 H
   H24        1.0     0.436453      0.159770      0.608728     Biso  1.000000 H
   H25        1.0     0.551701      0.358726      0.454268     Biso  1.000000 H
   H26        1.0     0.949486      0.661358      0.645320     Biso  1.000000 H
   H27        1.0     0.952580      0.751537      0.467078     Biso  1.000000 H
   H28        1.0     0.752143      0.601459      0.372029     Biso  1.000000 H
   K1         1.0     0.209972      0.447443      0.552994     Biso  1.000000 K
   K2         1.0     0.256789      0.084521      0.179527     Biso  1.000000 K
   K3         1.0     0.712376      0.988846      0.547488     Biso  1.000000 K
   K4         1.0     0.749766      0.623699      0.173753     Biso  1.000000 K
   K5         1.0     0.217819      0.267693      0.868463     Biso  1.000000 K
   K6         1.0     0.716457      0.804007      0.859901     Biso  1.000000 K
```

## 5. *Structure* ***PS–K$_3$Picene***

```
#======================================================================

# CRYSTAL DATA

#----------------------------------------------------------------------

STRUCTURE_PS_K3PC


_pd_phase_name                         'Herringbon                    '
_cell_length_a                         7.65312
_cell_length_b                         7.70746
_cell_length_c                         14.35388
_cell_angle_alpha                      90
_cell_angle_beta                       106.19752
_cell_angle_gamma                      90
_symmetry_space_group_name_H-M         'P 1'
_symmetry_Int_Tables_number            1

loop_
_symmetry_equiv_pos_as_xyz
   'x, y, z'

loop_
   _atom_site_label
   _atom_site_occupancy
   _atom_site_fract_x
   _atom_site_fract_y
   _atom_site_fract_z
   _atom_site_adp_type
   _atom_site_B_iso_or_equiv
   _atom_site_type_symbol
   C1         1.0     0.567357      0.257521      0.280362     Biso  1.000000 C
   C2         1.0     0.432643      0.757521      0.719638     Biso  1.000000 C
   C3         1.0     0.427028      0.144468      0.229183     Biso  1.000000 C
   C4         1.0     0.572972      0.644468      0.770817     Biso  1.000000 C
   C5         1.0     0.375462      0.130417      0.125692     Biso  1.000000 C
   C6         1.0     0.624538      0.630417      0.874308     Biso  1.000000 C
   C7         1.0     0.463733      0.233342      0.072753     Biso  1.000000 C
   C8         1.0     0.536267      0.733342      0.927247     Biso  1.000000 C
   C9         1.0     0.601271      0.350172      0.120170     Biso  1.000000 C
   C10        1.0     0.398729      0.850172      0.879830     Biso  1.000000 C
   C11        1.0     0.656389      0.366014      0.224391     Biso  1.000000 C
   C12        1.0     0.343611      0.866014      0.775609     Biso  1.000000 C
   C13        1.0     0.796463      0.479219      0.274527     Biso  1.000000 C
   C14        1.0     0.203537      0.979219      0.725473     Biso  1.000000 C
   C15        1.0     0.853035      0.487690      0.377907     Biso  1.000000 C
   C16        1.0     0.146965      0.987690      0.622093     Biso  1.000000 C
   C17        1.0     0.775786      0.382737      0.435551     Biso  1.000000 C
   C18        1.0     0.224214      0.882737      0.564449     Biso  1.000000 C
   C19        1.0     0.629348      0.264413      0.386719     Biso  1.000000 C
   C20        1.0     0.370652      0.764413      0.613281     Biso  1.000000 C
   C21        1.0     0.555026      0.153895      0.444207     Biso  1.000000 C
   C22        1.0     0.444974      0.653895      0.555793     Biso  1.000000 C
   C23        1.0     0.615529      0.155769      0.546912     Biso  1.000000 C
   C24        1.0     0.384471      0.655769      0.453088     Biso  1.000000 C
   C25        1.0     0.757597      0.264841      0.598741     Biso  1.000000 C
   C26        1.0     0.242403      0.764841      0.401259     Biso  1.000000 C
   C27        1.0     0.841834      0.382344      0.543474     Biso  1.000000 C
   C28        1.0     0.158166      0.882344      0.456526     Biso  1.000000 C
   C29        1.0     0.986056      0.486363      0.595128     Biso  1.000000 C
   C30        1.0     0.013944      0.986363      0.404872     Biso  1.000000 C
   C31        1.0     0.053102      0.481779      0.698469     Biso  1.000000 C
   C32        1.0     0.946898      0.981779      0.301531     Biso  1.000000 C
   C33        1.0     0.976641      0.369887      0.754639     Biso  1.000000 C
   C34        1.0     0.023359      0.869887      0.245361     Biso  1.000000 C
   C35        1.0     0.826556      0.257333      0.705006     Biso  1.000000 C
   C36        1.0     0.173444      0.757333      0.294994     Biso  1.000000 C
   C37        1.0     0.756822      0.140058      0.762021     Biso  1.000000 C
   C38        1.0     0.243178      0.640058      0.237979     Biso  1.000000 C
   C39        1.0     0.826558      0.130877      0.865296     Biso  1.000000 C
   C40        1.0     0.173442      0.630877      0.134705     Biso  1.000000 C
   C41        1.0     0.970398      0.239307      0.912300     Biso  1.000000 C
   C42        1.0     0.029602      0.739307      0.087700     Biso  1.000000 C
   C43        1.0     0.044220      0.358185      0.858701     Biso  1.000000 C
```

| | | | | | | |
|---|---|---|---|---|---|---|
| C44 | 1.0 | 0.955780 | 0.858185 | 0.141299 | Biso | 1.000000 C |
| H1 | 1.0 | 0.357794 | 0.061301 | 0.269270 | Biso | 1.000000 H |
| H2 | 1.0 | 0.642206 | 0.561301 | 0.730730 | Biso | 1.000000 H |
| H3 | 1.0 | 0.269535 | 0.038629 | 0.089086 | Biso | 1.000000 H |
| H4 | 1.0 | 0.730465 | 0.538629 | 0.910914 | Biso | 1.000000 H |
| H5 | 1.0 | 0.424606 | 0.222663 | 0.993859 | Biso | 1.000000 H |
| H6 | 1.0 | 0.575394 | 0.722663 | 0.006141 | Biso | 1.000000 H |
| H7 | 1.0 | 0.666096 | 0.432207 | 0.077026 | Biso | 1.000000 H |
| H8 | 1.0 | 0.333904 | 0.932207 | 0.922974 | Biso | 1.000000 H |
| H9 | 1.0 | 0.865762 | 0.560989 | 0.233704 | Biso | 1.000000 H |
| H10 | 1.0 | 0.134238 | 0.060989 | 0.766296 | Biso | 1.000000 H |
| H11 | 1.0 | 0.963246 | 0.578008 | 0.410145 | Biso | 1.000000 H |
| H12 | 1.0 | 0.036754 | 0.078008 | 0.589855 | Biso | 1.000000 H |
| H13 | 1.0 | 0.448163 | 0.061501 | 0.410103 | Biso | 1.000000 H |
| H14 | 1.0 | 0.551837 | 0.561501 | 0.589897 | Biso | 1.000000 H |
| H15 | 1.0 | 0.550427 | 0.065562 | 0.585538 | Biso | 1.000000 H |
| H16 | 1.0 | 0.449573 | 0.565562 | 0.414462 | Biso | 1.000000 H |
| H17 | 1.0 | 0.055437 | 0.574880 | 0.557872 | Biso | 1.000000 H |
| H18 | 1.0 | 0.944563 | 0.074880 | 0.442128 | Biso | 1.000000 H |
| H19 | 1.0 | 0.169008 | 0.564218 | 0.733373 | Biso | 1.000000 H |
| H20 | 1.0 | 0.830992 | 0.064218 | 0.266627 | Biso | 1.000000 H |
| H21 | 1.0 | 0.647428 | 0.050863 | 0.726742 | Biso | 1.000000 H |
| H22 | 1.0 | 0.352572 | 0.550863 | 0.273258 | Biso | 1.000000 H |
| H23 | 1.0 | 0.767833 | 0.039149 | 0.906405 | Biso | 1.000000 H |
| H24 | 1.0 | 0.232167 | 0.539149 | 0.093595 | Biso | 1.000000 H |
| H25 | 1.0 | 0.031640 | 0.228779 | 0.990349 | Biso | 1.000000 H |
| H26 | 1.0 | 0.968360 | 0.728779 | 0.009651 | Biso | 1.000000 H |
| H27 | 1.0 | 0.158331 | 0.440872 | 0.897286 | Biso | 1.000000 H |
| H28 | 1.0 | 0.841669 | 0.940872 | 0.102714 | Biso | 1.000000 H |
| K1 | 1.0 | 0.228169 | 0.306031 | 0.491218 | Biso | 1.000000 K |
| K2 | 1.0 | 0.771831 | 0.806031 | 0.508782 | Biso | 1.000000 K |
| K3 | 1.0 | 0.422623 | 0.289761 | 0.805023 | Biso | 1.000000 K |
| K4 | 1.0 | 0.577377 | 0.789761 | 0.194977 | Biso | 1.000000 K |
| K5 | 1.0 | 0.031107 | 0.273438 | 0.177182 | Biso | 1.000000 K |
| K6 | 1.0 | 0.968893 | 0.773438 | 0.822818 | Biso | 1.000000 K |